VICTREX AE ™ 250 LM PEAK with Hexcel AS4 12k Unitape 34% RC Material Allowables Statistical Analysis Report

NCAMP Project Number NPN 072001

NCAMP Report Number: NCP-RP-2021-015 N/C

Report Date: November 18, 2022

Elizabeth Clarkson, Ph.D.
National Center for Advanced Materials Performance (NCAMP)
National Institute for Aviation Research
Wichita State University
Wichita, KS 67260-0093

Testing Facility:

National Institute for Aviation Research
Wichita State University
1845 N. Fairmount
Wichita, KS 67260-0093

Test Panel Fabrication Facility:

TxV Aero Composites
55 Broadcommon Rd #2,
Bristol, RI 02809

Distribution Statement A. Approved for public release; distribution is unlimited.

Prepared by: Dr. Elizabeth Clarkson

Digitally signed by Dr. Elizabeth Clarkson
DN: cn=Dr. Elizabeth Clarkson, o=Wichita State University, ou=NCAMP, email=bclarkson@niar.wichita.edu, c=US
Date: 2022.11.21 12:05:42 -06'00'

Elizabeth Clarkson

Reviewed by: Nicole Stahl

Nicole Stahl

Michelle Man

Approved by: Royal Lovingfoss

Digitally signed by Royal Lovingfoss
Date: 2022.11.21 12:24:28 -06'00'

Royal Lovingfoss

Table of Contents

1. Introduction 9
1.1 Symbols and Abbreviations 10
1.2 Pooling Across Environments 12
1.3 Basis Value Computational Process 12
1.4 Modified Coefficient of Variation (CV) Method 12
2. Background 14
2.1 CMH17 STATS Statistical Formulas and Computations 14
2.1.1 Basic Descriptve Statistics 14
2.1.2 Statistics for Pooled Data 14
2.1.2.1 Pooled Standard Deviation 14
2.1.2.2 Pooled Coefficient of Variation 15
2.1.3 Basis Value Computations 15
2.1.3.1 K-factor computations 15
2.1.4 Modified Coefficient of Variation 16
2.1.4.1 Transformation of data based on Modified CV 17
2.1.5 Determination of Outliers 17
2.1.6 The k-Sample Anderson Darling Test for Batch Equivalency 18
2.1.7 r2oc665 (.)0.5 (.)0.5 D 68 >>BDC /TT0.21

e 7 Tc 0 Tw 2e-1.7 (t)0.7 (i)-5.2 (o)-Td [(2)-1.7 (.1)- (h.(h)4 (.52wT2 .8 (f)0.7 (O)3.1 (ut)0.7)Tj 0 Tc 0M T...)-1.7 (....157 Tw4 (.5
7 Tc 0 Tw 3e-1.7 (t)0.7 (i)-5.2 (o)-Td [(2)-1.7 (.1)- (h.(h)399.0/TT2 .8 (f)0.7 (O)3.>>BDC4.4 (...4.n5lM T...)-1.7 (....157 Tw399.0

4.6 Quasi Isotropic V-Notched Rail Shear (VNS1) 52
4.7 0° Flexure (FLEX) 54
4.8 Double Notched Shear (DNS) 57
4.9 Quasi Isotropic Double Notched Shear (DNS1) 59
4.10 Quasi Isotropic Unnotched Tension (UNT1) 61
4.11 “Soft” Unnotched Tension 2 (UNT2) 64
4.12 “Hard” Unnotched Tension 3 (UNT3) 66
4.13 Unnotched Compression 90/0 (UNC0) 69
4.14 Quasi Isotropic Unnotched Compression 1 (UNC1) 72
4.15 “Soft” Unnotched Compression 2 (UNC2) 74
4.16 “Hard” Unnotched Compression 3 (UNC3) 76
4.17 Quasi Isotropic Open-Hole Tension 1 (OHT1) 78
4.18 “Soft” Open-Hole Tension 2 (OHT2) 80
4.19 “Hard” Open-Hole Tension 3 (OHT3) 82
4.20 Quasi Isotropic Open-Hole Compression 1 (OHC1) 84
4.21 “Soft” Open-Hole Compression 2 (OHC2) 86
4.22 “Hard” Open-Hole Compression 3 (OHC3) 88
4.23 Quasi Isotropic Filled-Hole Tension 1 (FHT1) 90
4.24 “Soft” Filled-Hole Tension 2 (FHT2) 92
4.25 “Hard” Filled-Hole Tension 3 (FHT3) 94
4.26 Quasi Isotropic Filled-Hole Compression 1 (FHC1) 96
4.27 “Soft” Filled-Hole Compression 2 (FHC2) 98
4.28 “Hard” Filled-Hole Compression 3 (FHC3) 100
4.29 Quasi Isotropic Single-Shear Bearing 1 (SSB1) 102
4.30 “Soft” Single-Shear Bearing 2 (SSB2) 105
4.31 “Hard” Single-Shear Bearing 3 (SSB3) 107
4.32 Quasi Isotropic Compression After Impact 1 (CAI1) 109
4.33 Interlaminar Tension and Curved Beam Strength (ILT and CBS) 110
5. Outliers 111
6. References 113

List of Figures

Figure 4-1 Batch plot for LT strength normalized 39
Figure 4-2 Batch plot for LC strength normalized 42
Figure 4-3: Batch Plot for TC strength asmeasured 44
Figure 4-4: Batch plot for IPS for 0.2% Offset Strength and Strength at 5% Strain as measured 47
Figure 4-5: Batch plot for VNS for 0.2% Offset Strength and Strength at 5% Strain as measured 50
Figure 4-6: Batch plot for VNS1 for Ultimate Strength asmeasured 52
Figure 4-7: Batch Plot for Flexure strength normalized 55
Figure 4-8: Batch Plot for DNS strength normalized 57
Figure 4-9: Batch Plot for DNS1 strength normalized 59
Figure 4-10: Batch Plot for UNT1 strength normalized 62
Figure 4-11: Batch Plot for UNT2 strength normalized 64
Figure 4-12: Batch Plot for UNT3 strength normalized 67
Figure 4-13: Batch Plot for UNC1 strength normalized 70
Figure 4-14: Batch u18d ( )Tj 0.01 0 Td (.....)Tj (.....)Tj ( )Tj 16.21 0 T

Table 4-34: Statistics and Basis Values for OHC1 Strength data 85
Table 4-35: Statistics and Basis Values for OHC2 Strength data 87
Table 4-36: Statistics and Basis Values for OHC3 Strength data 89
Table 4-37: Statistics and Basis Values for FHT1 Strength data 91
Table 4-38: Statistics and Basis Values for FHT2 Strength data 93
Table 4-39: Statistics and Basis Values for FHT3 Strength data 95
Table 4-40: Statistics and Basis Values for FHC1 Strength data 97
Table 4-41: Statistics and Basis Values for FHC2 Strength data 99
Table 4-42: Statistics and Basis Values for FHC3 Strength data 101
Table 4-43: Statistics and Basis Values for SSB1 2% Offset Strength data 104
Table 4-44: Statistics and Basis Values for SSB1 Ultimate Strength data 104
Table 4-45: Statistics and Basis Values for SSB2 Strength data 106
Table 4-46: Statistics and Basis Values for SSB3 Strength data 108
Table 4-47: Statistics for Compression After Impact Strength data 109
Table 4-48: Statistics for ILT and CBS Strength data 110
Table 5-1: List of Outliers 112

1. Introduction

This report contains statistical analysis of the VICTREX AE^{TM} 250 T-071 unidirectional tape prepreg material property data published in NCAMP Test Report CAM-RP-2021-025 N/C. The lamina and laminate material property data have been generated in accordance with NCAMP Standard Operating Procedures NSP 100. The test panels, test specimens, and test setups have been conformed by an NCAMP appointed AIR and the testing has been witnessed by an NCAMP AER.

process known as equivalency. More information about this equivalency process including the test statistics and its limitations can be found in Section 6 of DOT/FAA/AR-03/19 and Section 8.4.1 of CMH-17-1G. The applicability of equivalency process must be evaluated on program-by-program basis by the applicant and certifying agency. The applicant and certifying agency must agree that the equivalency test plan along with the equivalency process described in Section 6 of DOT/FAA/AR-03/19 and Section 8.4.1 of CMH-17-1G are adequate for the given program.

Aircraft companies should not use the data published in this report without specifying NCAMP Material Specification NMS 125/1. NMS 125/1 has additional requirements that are listed in its prepreg process control document (PCD), fiber specification, fiber PCD, and other raw material specifications and PCDs which impose essential quality controls on the raw materials and raw material manufacturing equipment and processes. *Aircraft companies and certifying agencies should assume that the material property data published in this report is not applicable when the material is not procured to NCAMP Material Specification NMS 125/1.*

sps1 (not)-rMaport 3-2 (s31 (not)-(r

Test Property	Symbol
Longitudinal Compression Strength	F_1^{cu}
Longitudinal Compression Modulus	E_1^{c}
Longitudinal Tension Strength	F_1^{tu}
Longitudinal Tension Modulus	E_1^{t}
Longitudinal Tension Poisson's Ratio	$_{12}^{t}$
Transverse Compression Strength	F_2^{cu}
Transverse Compression Modulus	E_2^{c}
Transverse Tension Strength	F_2^{tu}
Transverse Tension Modulus	E_2^{t}

1.2 Pooling Across Environments

When pooling across environments was allowable, the pooled coefficient of variation was used. CMH17 STATS (CMH17 Approved Statistical Analysis Program) was used to determine if pooling was allowable and to compute the pooled coefficient of variation for those tests. In these cases, the modified coefficient of variation based on the pooled data was used to compute the basis values.

When pooling across environments was not advisable because the data was not eligible for pooling and engineering judgment indicated there was justification for overriding the result, then B-Basis values were computed for each environmental condition separately which are also provided by CMH17 STATS.

1.3 Basis Value Computational Process

The general form to compute engineering basis values is: basis value $= \bar{X} - kS$ where k is a factor based on the sample size and the distribution of the sample data. There are many different methods to determine the value of k in this equation, depending on the sample size and the distribution of the data. In addition, the computational formula used for the standard deviation, S, may vary depending on the distribution of the data. The details of those different computations and when each should be used are in section 2.0.

1.4 Modified Coefficient of Variation (CV) Method

A common problem with new material qualifications is that the initial specimens produced and tested do not contain all of the variability that will be encountered when the material is being produced in larger amounts over a lengthy period of time. This can result in setting basis values that are unrealistically high. The variability as measured in the qualification program is often lower than the actual material variability because of several reasons. The materials used in the qualification programs are usually manufactured within a short period of time, typically 3 2 ng on tton m ( )]TJ 0.36 TnTw -38.g (l)-1 (i)4

2. Background

Statistical computations are performed with CMH17 STATS. Pooling across environments will be used whenever it is permissible according to CMH17-1G guidelines. If pooling is not permissible, the results of a single point analysis provided by CMH17 STATS is included instead. If the data does not meet CMH17-1G requirements for a single point analysis, estimates are created by a variety of methods depending on which is most appropriate for the dataset available. Specific procedures used are presented in the individual sections where the data is presented.

2.1 CMH17 STATS Statistical Formulas and Computations

This section contains the details of the specific formulas CMH17 STATS uses in its computations.

2.1.1 Basic Descriptive Statistics

The basic descriptive statistics shown are computed according to the usual formulas, which are shown below:

Mean: $$\bar{X} = \sum_{i=1}^{n} \frac{X_i}{n}$$ **Equation 1**

Std. Dev.: $$S = \sqrt{\frac{1}{n-1} \sum_{i=1}^{n} \left(X_i - \bar{X} \right)^2}$$ **Equation 2**

% Co. Variation: $$\frac{S}{\bar{X}} \times 100$$ **Equation 3**

Where n refers to the number of specimens in the sample and X_i refers to the individual specimen measurements.

2.1.2 Statistics for Pooled Data

Prior to computing statistics for the pooled dataset, the data is normalized to a mean of one by dividing each value by the mean of all the data for that condition. This transformation does not affect the coefficients of variation for the individual conditions.

2.1.2.1 Pooled Standard Deviation

The formula to compute a pooled standard deviation is given below:

$$N = \sum_{j=1}^{r} n_j$$

I 1 í U

$$\frac{2.323}{\sqrt{}} \quad \frac{1.064}{} \quad \frac{0.9157}{\sqrt{}} \quad \frac{0.653}{2}$$

2.1.4.1 Transformation of data based on Modified CV

In order to determine if the data would pass the diagnostic tests under the assumption of the modified CV, the data must be transformed such that the batch means remain the same while the standard deviation of transformed data (all batches) matches the modified standard deviation.

To accomplish this requires a transformation in two steps:

Step 1: Apply the modified CV rules to each batch and compute the modified standard deviation $S_i^* = CV^* \cdot \bar{X}_i$ for each batch. Transform the individual data values (X_{ij}) in each batch as follows:

$$\left(\qquad \bar{} \right)$$

$$MNR = \frac{\max_{all\ i} \left| X_i - \bar{X} \right|}{S}, i = 1 \quad n$$ **Equation 23**

$$C = \frac{n-1}{\sqrt{n}} \sqrt{\frac{t^2}{n-2+t^2}}$$ **Equation 24**

where t is the $1 - \frac{.05}{2n}$ freedom, n being the total number of data values.

If MNR > C, then the X_i associated with the MNR is considered to be an outlier. If an outlier exists, then the X_i associated with the MNR is dropped from the n dataset and the MNR procedure is applied again. This process is repeated until no outliers are detected. Additional information

ÐÏà¡±á @ ÿþ Root Entry Ñ Workbook ÿÿÿÿ Summary Information ÿÿÿÿ Document Summary Information ÿÿÿÿ

$$^{2} \quad (\quad) \quad \frac{^{3} \quad ^{2}}{(\quad 1)(\quad 2)(\quad 3)(\quad 1)^{2}}$$

Where F0 is the standard normal distribution function. The observed significance level (OSL) is

$$OSL = \frac{1}{1 + e^{-0.48 + 0.78\ln(AD^*) + 4.58AD^*}}, \quad AD^* = \left(1 + \frac{4}{n} - \frac{25}{n^2}\right)AD$$ **Equation 31**

This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if, in fact, the data are a sample from a normal population. If OSL > 0.05, the data is considered sufficiently close to a normal distribution.

2.1.8 Levene's Test for Equality of Coefficient of Variation

Levene's test performs an Analysis of Variance on the absolute deviations from the sample medians. The absolute value of the deviation from the median is computed for each data value. $w_{ij} = \left| y_{ij} - y_i \right|$ An F-test is then performed on the transformed data values as follows:

$$F = \frac{\sum_{i=1}^{k} n_i \left(\overline{w}_i - \overline{w}\right)^2 / (k-1)}{\sum_{i=1}^{k}\sum_{j=1}^{n_i} \left(w_{ij} - \overline{w}_i\right)^2 / (n-k)}$$ **Equation 32**

If this computed F statistic is less than the critical value for the F distribution having k-1 numerator and n-

If the normal distribution has an OSL greater than 0.05, then the data is assumed to be from a population with a normal distribution. If not, then if either the Weibull or lognormal distributions has an OSL greater than 0.05, then one of those can be used. If neither of these distributions has an OSL greater than 0.05, a nonparametric approach is used.

In what follows, unless otherwise noted, the sample size is denoted by n, the sample observations by $x_1, \ldots, x_n$, and the sample observations ordered from least to greatest by $x_{(1)}, \ldots, x_{(n)}$.

2.1.9.1 One-sided B-basis tolerance factors, k_B, for the normal distribution when sample size is greater than 15.

The exact computation of k_B values is $1/\sqrt{n}$ times the 0.95th quantile of the noncentral t-distribution with noncentrality parameter $1.282\sqrt{n}$ and degrees of freedom. Since this is not a calculation that Excel can handle, the following approximation to the k_B values is used:

$$k_B \approx 1.282 + \exp\{0.958 - 0.520\ln(n) - 3.19/n\} \qquad \textbf{Equation 33}$$

This approximation is accurate to within 0.2% of the tabulated values for sample sizes greater than or equal to 16.

2.1.9.2 One-sided A-basis tolerance factors, k_A, for the normal distribution

The exact computation of k_A values is $1/\sqrt{n}$ times the 0.95th quantile of the noncentral t-distribution with noncentrality parameter $2.326\sqrt{n}$ and

In order to compute a check of the fit of a data set to the Weibull distribution and compute basis values assuming Weibull, it is first necessary to obtain estimates of the population shape and scale parameters (Section 2.1.9.3.1). Calculations specific to the goodness-of-fit test for the Weibull distribution are provided in section 2.1.9.3.2.

2.1.9.3.1 Estimating Weibull Parameters

This section describes the *maximum likelihood* method for estimating the parameters of the two-parameter Weibull distribution. The maximum-likelihood estimates of the shape and scale parameters are denoted $\hat{\beta}$ and $\hat{\alpha}$. The estimates are the solution to the pair of equations:

$$\frac{n}{\hat{\beta}} + \sum_{i=1}^{n} \ln x_i - \frac{\sum_{i=1}^{n} x_i^{\hat{\beta}} \ln x_i}{\sum_{i=1}^{n} x_i^{\hat{\beta}}} = 0 \qquad \textbf{Equation 36}$$

$$\hat{\alpha} = \left(\frac{1}{n} \sum_{i=1}^{n} x_i^{\hat{\beta}} \right)^{1/\hat{\beta}}$$

2.1.9.3.2 Goodness-of-fit test for the Weibull distribution

The two-parameter Weibull distribution is considered by comparing the cumulative Weibull distribution function that best fits the data with the cumulative distribution function of the data. Using the shape and scale parameter estimates from section 2.1.9.3.1, let

$$z_{(i)} = \left[x_{(i)} / \hat{\alpha} \right]^{\hat{\beta}}, \quad \text{for } i = 1, \ldots, n \qquad \textbf{Equation 38}$$

The Anderson-Darling test statistic is

$$AD = \sum_{i=1}^{n} \frac{1-2i}{n} \left[\ln\left[1 - \exp(-z_{(i)})\right] - z_{(n+1-i)} \right] - n \qquad \textbf{Equation 39}$$

and the observed significance level is

$$OSL = 1 / \left\{ 1 + \exp[-0.10 + 1.24 \ln(AD^*) + 4.48 AD^*] \right\} \qquad \textbf{Equation 40}$$

where

$$AD^* = \left(1 + \frac{0.2}{\sqrt{n}} \right) AD \qquad \textbf{Equation 41}$$

This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if in fact the data is a sample from a two-parameter Weibull distribution. If $OSL \leq 0.05$, one may conclude (at a five percent risk of being in error) that the population does not have a two-parameter Weibull distribution. Otherwise, the hypothesis that the population has a two-parameter

$$V_A \approx 6.649 + \exp\left[2.55 - 0.526\ln\left(n + \frac{4.76}{n}\right)\right] \quad \text{Equation 46}$$

This approximation is accurate within 0.5% of the tabulated values for n greater than or equal to 16.

Weibull Dist. K Factors for N<16		
N	B-basis	A-basis
2	690.804	1284.895
3	47.318	88.011
4	19.836	36.895
5	13.145	24.45
6	10.392	19.329
7	8.937	16.623
8	8.047	14.967
9	7.449	13.855
10	6.711	12.573
11	6.477	12.093
12	6.286	11.701
13	6.127	11.375
14	5.992	11.098
15	5.875	10.861

Table 2-1: Weibull Distribution Basis Value Factors

2.1.9.4 Lognormal Distribution

A probability distribution for which the probability that an observation selected at random from this population falls between a and b $(0 < a < b < \infty)$ is given by the area under the normal distribution between ln(a) and ln(b).

The lognormal distribution is a positively skewed distribution that is simply related to the normal distribution. If something is lognormally distributed, then its logarithm is normally distributed. The natural (base e) logarithm is used.

2.1.9.4.1 Goodness-of-fit test for the Lognormal distribution

In order to test the goodness-of-fit of the lognormal distribution, take the logarithm of the data and perform the Anderson-Darling test for normality from Section 2.1.7. Using the natural logarithm, replace Equation 29 above with Equation 47 below

$$z_{(i)} = \frac{\ln\left(x_{(i)}\right) - \bar{x}_L}{s_L}, \quad \text{for } i = 1, \ldots, n \quad \text{Equation 47}$$

where $x_{(i)}$ is the i^{th} smallest sample observation, $\bar{x}_L$ and s_L are the mean and standard deviation of the ln(x) values.

The Anderson-Darling statistic is then computed using Equation 30 above and the observed significance level (OSL) is computed using Equation 31 above. This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if in fact the data are a sample from a lognormal distribution. If OSL ≤ 0.05, one may conclude

2.1.10.2 Non-parametric Basis Values for small samples

The Hanson-Koopmans method (reference 8 and 9) is used for obtaining a B-Basis value for sample sizes not exceeding 28 and A-Basis values for sample sizes less than 299. This procedure requires the assumption that the observations are a random sample from a population for which the logarithm of the cumulative distribution function is concave, an assumption satisfied by a large class of probability distributions. There is substantial empirical evidence that suggests that composite strength data satisfies this assumption.

The Hanson-Koopmans B-basis value is:

B-Basis Hanson-Koopmans Table		
n	r	k
2	2	35.177
3	3	7.859
4	4	4.505
5	4	4.101
6	5	3.064
7	5	2.858
8	6	2.382
9	6	2.253
10	6	2.137
11	7	1.897
12	7	1.814
13	7	1.738
14	8	1.599
15	8	1.540
16	8	1.485
17	8	1.434
18	9	1.354
19	9	1.311
20	10	1.253
21	10	1.218
22	10	1.184
23	11	1.143
24	11	1.114
25	11	1.087
26	11	1.060
27	11	1.035
28	12	1.010

Table 2-2: B-Basis Hanson-Koopmans Table

n	k	n	k	n	k
2	80.00380	38	1.79301	96	1.32324
3	16.91220	39	1.77546	98	1.31553
4	9.49579	40	1.75868	100	1.30806
5	6.89049	41	1.74260	105	1.29036
6	5.57681	42	1.72718	110	1.27392
7	4.78352	43	1.71239	115	1.25859

4.

1104. 1104. 1. 1104.

2.1.11.1Calculation of basis values using ANOVA

The following calculations address batch-to-

2.4 0º Lamina Strength Derivation

Lamina strength values in the 0º direction were not obtained directly for any conditions during compression tests. They are derived from the cross-ply lamina test results using a back out formula. Unless stated otherwise, the 0° lamina strength values were derived using the following formula:

$F_0^u = F_{0/90}^u \cdot BF$ where BF is the backout factor.

$F_{0/90}^u$ =UNC0 or UNT0 strength valu

3. Summary of Results

The basis values for all tests are summarized in the following tables. The NCAMP recommended B-basis values meet all requirements of CMH-17-1G. However, not all test data meets those requirements. The summary tables provide a complete listing of all computed basis values and estimates of basis values. Data that does not meet the requirements of CMH-17-1G are shown in shaded boxes and labeled as estimates. Basis values computed with the modified coefficient of variation (CV) are presented whenever possible. Basis values and estimates computed without that modification are presented for all tests.

3.1 NCAMP Recommended B-basis Values

The following rules are used in determining what basis value, if any, is included in tables Table 3-1 and Table 3-2 of recommended values.

1. Recommended values are NEVER estimates. Only B-basis values that meet all requirements of CMH-17-1G are recommended.
2. Modified CV basis values are preferred. Recommended values will be the modified CV basis value when available. The CV provided with the recommended basis value will be the one used in the computation of the basis value.
3. Only normalized basis values are given for properties that are normalized.
4. ANOVA B-basis values are not recommended since only three batches of material are available and CMH-17-1G recommends that no less than five batches be used when computing basis values with the ANOVA method.
5. Basis values of 90% or more of the mean value imply that the CV is unusually low and may not be conservative. Caution is recommended with B-basis values calculated from CMH-17 STATS when the B-basis value is 90% or more of the average value. Such values will be indicated.
6. If the data appear questionable (e.g. when the CTA-RTA-ETW trend of the basis values is not consistent with the CTA-RTA-ETW trend of the average values), then the B-basis values will not be recommended.

Lamina Strength (ksi) Tests

					0.2% Offset	5% Strain	0.2% Offset	5% Strain		
B-basis	304.0	201.9	33.48***	12.72	6.071	11.53	5.875	10.93	207.7	107.9
Mean	342.6	225.6	37.07	14.25	6.745	12.76	6.514	12.10	232.6	120.6
CV	6.000	6.017	6.000	6.650	6.000	6.000	6.000	6.000	6.000	6.017
B-basis	271.7	184.0	24.40	10.47	4.861	8.181	4.466	7.886	172.2	98.95
Mean	310.1	207.7								

NCAMP Recommended B-basis Values for

Victrex AE™ 250 LM PAEK, AS4 12k Unitape 143 gsm 34% RC

All B-basis values in this table meet the standards for publication in CMH-17G Handbook

Values are for normalized data unless otherwise noted

Lamina Strength (ksi) Tests

Lay-up	ENV	Statistic	OHT	OHC	FHT	FHC	UNT	UNC	SSB 2% Offset	SSB Ultimate	VNS*	DNS*
Quasi Isotropic	CTA (-65 öF)	B-basis	51.95		57.36		107.2					
		Mean	58.22		64.13		120.1					
		CV	6.000		6.000		6.000					
	RTA (70 öF)	B-basis	50.33	40.17	52.88	65.98	102.6	71.73	95.38	109.9	36.60	NA: A
		Mean	56.60	45.57	59.65	74.84	115.4	81.36	108.5	124.7	42.92	10.17
		CV	6.000	6.000	6.000	6.000	6.000	6.000	6.129	6.000	7.642	6.113
	ETW2 (250 öF)	B-basis		30.78				58.68				
		Mean		34.91				66.56				
		CV		6.000				6.000				
	ETW (275 öF)	B-basis	45.12	27.29	53.02**	45.36	90.79	53.08	76.55	82.53	21.34	4.954
		Mean	51.18	30.95	54.65	51.45	103.0	61.08	87.69	94.63	30.36	5.783
		CV	6.000	6.000	1.863	6.000	6.000	6.637	6.435	6.479	15.24	7.258
"Soft"	CTA (-65 öF)	B-basis	43.28		48.68		63.02					
		Mean	47.85		53.66		69.61					
		CV	6.241		6.255		6.000					
	RTA (70 öF)	B-basis	39.46	38.17	42.11	51.69	56.22	52.71	99.11	120.2		
		Mean	44.02	42.09	47.09	57.09	62.77	58.36	110.0	132.7		
		CV	6.083	6.000	6.000	6.000	6.000	6.000	6.000	6.000		
	ETW (275 öF)	B-basis	28.17	24.37	30.26	32.35	45.94	34.83	73.66	80.29		
		Mean	32.73	28.29	35.24	37.75	52.52	40.48	84.52	92.81		
		CV	6.000	6.000	6.000	6.401	6.000	6.522	6.202	6.000		
"Hard"	CTA (-65 öF)	B-basis	69.35		NA: A		149.5					
		Mean	78.39		83.79		166.9					
		CV	6.571		4.665		6.000					
	RTA (70 öF)	B-basis	69.09	50.25	NA: A	81.16	150.3	98.25	95.36	115.1		
		Mean	78.08	57.27	79.85	89.56	167.7	108.8	109.3	127.0		
		CV	6.150	6.296	3.884	6.000	6.000	6.000	6.000	6.000		
	ETW (275 öF)	B-basis	NA: A	34.56	66.32	53.65	140.3	64.60	66.90	78.28		
		Mean	75.28	39.39	75.23	62.09	157.6	75.14	80.77	90.19		
		CV	4.603	6.206	6.000	6.000	6.000	6.562	10.63	6.030		

Notes: The modified CV B-basis value is recommended when available.
The CV provided corresponds with the B-basis value given.
NA implies that tests were run but data did not meet NCAMP recommended requirements.
"NA: A" indicates ANOVA with 3 batches, "NA: I" indicates insufficient data,
Shaded empty boxes indicate that no test data is available for that property and condition.
* Data is as-measured rather than normalized
** indicates the Single Point B-basis value is greater than 90% of the mean value.

3.2 Lamina and Laminate Summary Tables

4. Test Results, Statistics, Basis Values, and Graphs

Test data for fiber dominated properties was normalized according to nominal cured ply thickness. Both normalized and as-measured statistics were included in the tables, but only the normalized data values were graphed. Test failures, outliers and explanations regarding computational choices were noted in the accompanying text for each test.

All individual specimen results are graphed for each test by batch and environmental condition with a line indicating the recommended basis values for each environmental condition. The data is jittered (moved slightly to the left or right) in order for all specimen values to be clearly visible. The strength values are always graphed on the vertical axis with the scale adjusted to include all data values and their corresponding basis values. The vertical axis may not include zero. The horizontal axis values will vary depending on the data and how much overlapping there was of the data within and between batches. When there was little variation, the batches were graphed from left to right. The environmental conditions were identified by the shape and color of the symbol used to plot the data. Otherwise, the environmental conditions were graphed from left to right and the batches were identified by the shape and color of the symbol.

4.1 Longitudinal Tension (LT)

Longitudinal Tension data is normalized, so both normalized and measured values are provided. Data is available for two properties, strength and modulus. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition.

The ETW datasets, both normalized and measured, failed the Anderson-Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. These datasets failed the ADK test after applying the modified CV transformation to the data. Estimates were below zero using the ANOVA method and are indicated with NA for that reason. Pooling the CTA and RTA conditions was acceptable for the modified CV basis values for both normalized and measured datasets.

There were no statistical outliers.

Statistics and basis values are given for strength data in Table 4-1 and for the modulus data in Table 4-2. The data and the B-basis values are shown graphically in Figure 4-1.

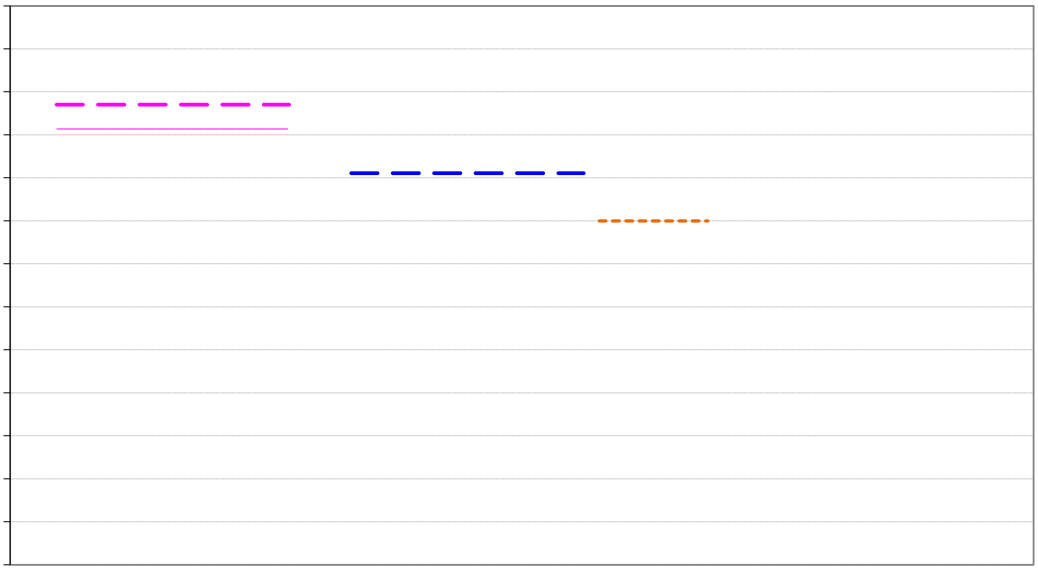

Longitudinal Tension Strength Basis Values and Statistics

	Normalized				As-measured			
Env	**CTA**	**RTA**	**ETA**	**ETW**	**CTA**	**RTA**	**ETA**	**ETW**
Mean	342.6	310.1	282.7	272.1	357.1	320.4	297.9	281.1
Stdev	10.88	18.89	14.11	23.40	15.64	23.44	16.94	26.27
CV	3.175	6.094	4.992	8.600	4.380	7.317	5.685	9.346
Mod CV	6.000	7.047	8.000	8.600	6.190	7.658	8.000	9.346
Min	322.5	281.0	265.4	225.3	333.2	291.4	277.5	228.8
Max	364.7	346.6	296.2	312.1	381.2	370.6	314.1	324.3
No. Batches	3	3	1	3	3	3	1	3
No. Spec.	18	19	6	19	18	19	6	19
B-basis Value	321.1	273.2				274.7		
B-Estimate			239.9	129.1	280.2		246.6	115.1
A-estimate	305.9	247.1	209.5	27.08	225.3	242.2	210.1	NA
Method	Normal	Normal	Normal	ANOVA	ANOVA	Normal	Normal	ANOVA
B-basis Value	304.0	271.7			314.6	278.1		
B-Estimate			214.5				226.1	
A-estimate	277.8	245.4	167.9		285.7	249.2	177.0	
Method	pooled	pooled	normal		pooled	pooled	normal	

4.2 Longitudinal Compression (LC)

Longitudinal Compression data is normalized, so both normalized and measured values are provided.

Env.916.21	CTA	RTA	ETA	ETW	CTA	RTA	ETA	ETW
Mean	16.72	16.91	17.38	17.24	17.38	17.58	18.00	17.70
Stdev	0.3416	0.2533	0.1479	0.2327	0.2878	0.2476	0.1623	0.2830
CV	2.043	1.498	0.8512	1.350	1.656	1.408	0.9014	1.598
Mod CV	6.000	6.000	8.000	6.000	6.000	6.000	8.000	6.000
Min	15.90	16.21	17.6 (8 0 TdN16.)-5.7 (21)]TJ 5.545Tw 36d16.21					

4.3 TransverseCompression(TC)

The Transverse Compression data is not normalized. Data is available for two properties, strength and modulus. The ETA dataset lacked sufficient specimens to meet 17 CMH guidelines, so only estimates are provided for that condition. The CTA dataset failed normality but the Weibull distribution provided the best fit for the dataset. However, the pooled dataset passed the normality test after applying the modified CV transformation to the data, so modified CV basis values could be computed for CTA and RTA conditions. The modified CV CTA and RTA conditions met all requirements for pooling, so those two datasets were pooled to compute the modified CV basis values and estimates.

fotoor CTA A ailThwo

Transverse Compression Strength Basis Values and Statistics				
As-measured				
Env	**CTA**	**RTA**	**ETA**	**ETW**
Mean	37.07	27.99	15.29	14.16
Stdev	1.440	0.5670	0.3349	0.3114
CV	3.884	2.025	2.191	2.199
Mod CV	6.000	6.000	8.000	6.000
Min	32.96	26.98	15.01	13.60
Max	38.49	29.08	15.89	14.79
No. Batches	3	3	1	3
No. Spec.	18	18	6	18
Basis Values and Estimates				
B-basis Value	34.51	26.87		13.54
B-estimate			14.27	
A-estimate	31.73	26.08	13.55	13.11
Method	Weibull	Normal	Normal	Normal
Modified CV Basis Values and Estimates				
B-basis Value	33.48	24.40		12.48
B-estimate			11.60	
A-estimate	31.04	21.96	9.083	11.30
Method	pooled	pooled	normal	normal

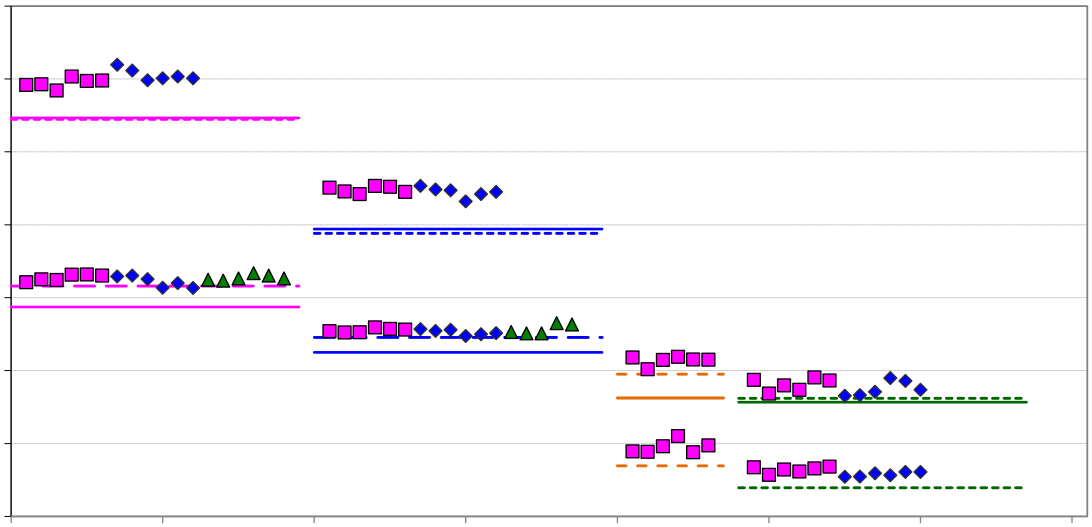

18

In Plane Shear Modulus Statistics

Modulus Statistics

Env	CTA	RTA	ETA	ETW
Mean	0.7000	0.6562	0.4991	0.3590
Stdev	0.00875	0.01179	0.03104	0.02275
CV	1.250	1.796	6.219	6.337
Mod CV	6.000	6.000	8.000	7.168
Min	0.6859	0.6330	0.4688	0.3084
Max	0.7159	0.6728	0.5533	0.3934
No. Batches	3	3	1	3
No. Spec.	18	18	6	18

4.5 V-Notched Rail Shear (VNS)

The V-Notched Rail Shear data is not normalized. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only tentative estimates are provided for that condition. Data is provided on three different properties, 0.2% Offset Strength, Strength at 5% Strain and Modulus.

The CTA and RTA conditions for the 0.2% Offset Strength met all requirements for pooling.

The CTA and RT

V-Notched Rail Shear Modulus Statistics				
Modulus Statistics				
Env	CTA	RTA	ETA	ETW
Mean	0.7119	0.6715	0.5826	0.4211
Stdev	0.01068	0.008319	0.01457	0.05666
CV	1.500	1.239	2.501	13.45
Mod CV	6.000	6.000	8.000	13.45
Min	0.6922	0.6571	0.5682	0.3155
Max	0.7356	0.6881	0.6059	0.5284
No. Batches	3	3	1	3
No. Spec.	18	18	6	21

Table 4-10: Statistics from VNS Modulus data

4.6 Quasi Isotropic V-Notched Rail Shear (VNS1)

The VNS1 data is not normalized. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition. Data is provided on two properties, Ultimate Shear Strength and Modulus.

There were no diagnostic test failures. Pooling was not acceptable due to the insufficient number of specimens in the ETA condition.

There was one statistical outlier. The largest value in batch one of the ETA condition was an outlier for batch one only, not for the RTA condition. It was retained for this analysis.

Statistics, estimates and basis values are given for the ultimate shear strength properties data in Table 4-11, and modulus data in Table 4-12. The data, B-estimates and B-basis values for strength are shown graphically in Figure 4-6.

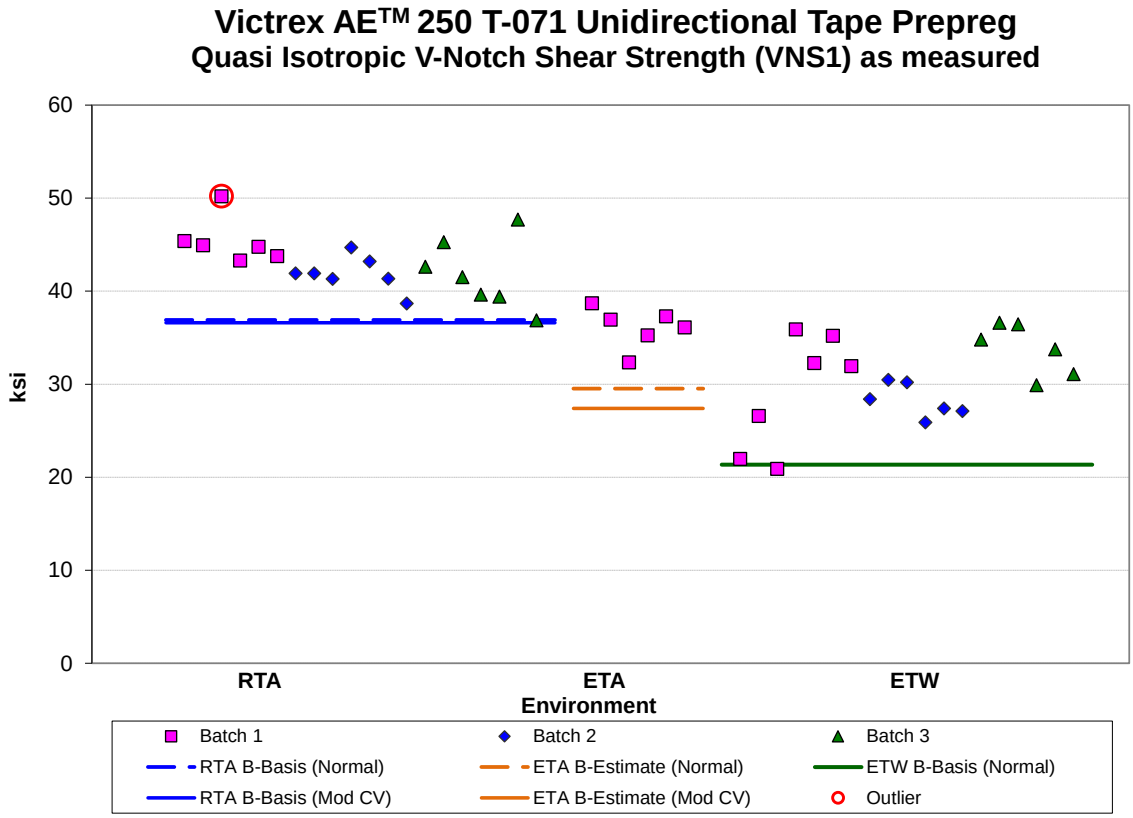

Figure 4-6: Batch plot for VNS1 for Ultimate Strength as-measured

Quasi Isotropic V-Notched Rail Shear Ultimate Strength Basis Values and Statistics			
As-measured			
Env	RTA	ETA	ETW
Mean	42.92	36.11	30.36
Stdev	3.126	2.172	4.626
CV	7.285	6.017	15.24
Mod CV	7.642	8.000	15.24
Min	36.86	32.35	20.91
Max	50.19	38.69	36.61
No. Batches	3	1	3
No. Spec.	20	6	19
Basis Values and Estimates			
B-basis Value	36.90		21.34
B-estimate		29.53	
A-estimate	32.61	24.85	14.94
Method	Normal	Normal	Normal
Modified CV Basis Values and Estimates			
B-basis Value	36.60		NA
B-estimate		27.40	
A-estimate	32.11	21.45	
Method	normal	normal	

4.7 0° Flexure (FLEX)

The Flexure data is normalized, so statistics for both as-measured and normalized are provided. Data is available for only for one property, strength. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition. Tests were run in both the 0° and 90° directions.

The 90° direction tests were run only in the RTA condition. No basis values could be provided for the 90° direction results because both the normalized and as-measured datasets failed the Anderson Darling k-sample test (ADK test) for batch to batch variability and CMH-17 Rev G guidelines required using the ANOVA analysis. Thd us.e1 (Dhe)92 (i)-2 (m (qui)-2 -)-2 - coulTseasu co

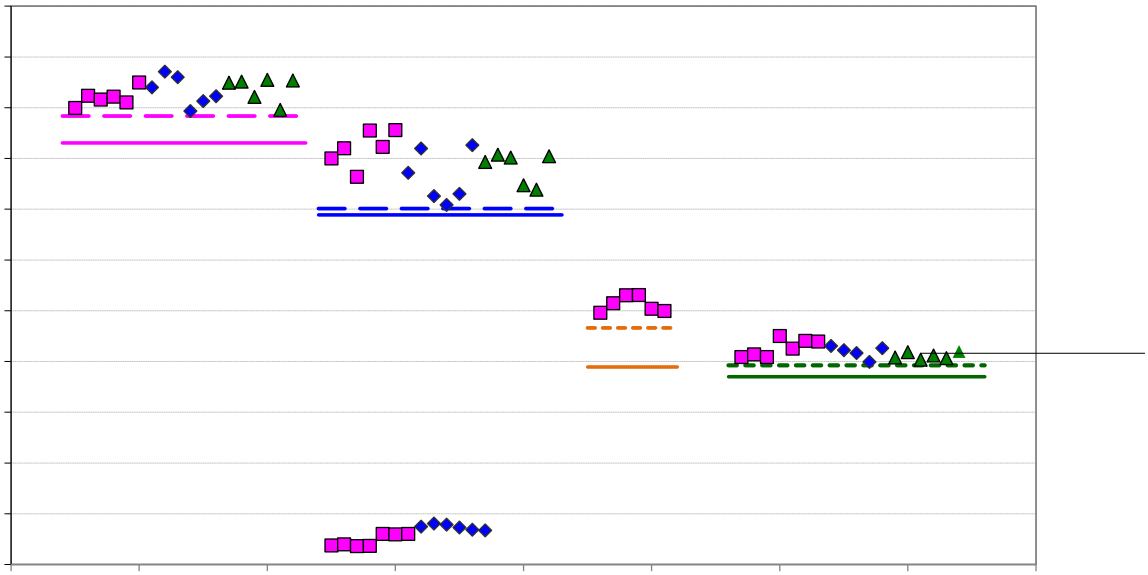

90° Flexure Strength Statistics		
RTA Condition		
Env	Norm	As-meas
Mean	15.39	15.81
Stdev	3.485	3.512
CV	22.64	22.22
Mod CV	22.64	22.22
Min	9.120	9.483
Max	20.21	20.69
No. Batches	3	3
No. Spec.	19	19

Table 4-14: Statistics from 90° Flexure Strength data

4.8 Double Notched Shear (DNS)

The Double Notched Shear data is not normalized. Data is available for only one property, strength. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition.

The CTA and RTA datasets failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH 17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When the CTA and RTA datasets were transformed according to the assumptions of the modified CV method, they both passed the ADK test, so the modified CV basis values are provided. These datasets met all requirements for pooling.

There were no statistical outliers.

Statistics, basis values and estimates are given for StbaStd

Double Notched Shear Strength Basis Values and Statistics				
As-measured				
Env	CTA	RTA	ETA	ETW
Mean	14.25	12.01	6.660	6.670
Stdev	0.7554	0.4257	0.2705	0.3191
CV	5.300	3.545	4.061	4.784
Mod CV	6.650	6.000	8.000	6.392
Min	12.46	11.06	6.349	6.050
Max	15.27	12.62	6.981	7.246
No. Batches	3	3	1	3
No. Spec.	18	18	6	18
Basis Values and Estimates				
B-basis Value				6.040
B-estimate	10.31	9.458	5.841	
A-estimate	7.505	7.639	5.258	5.594
Method	ANOVA	ANOVA	Normal	Normal
Modified CV Basis Values and Estimates				
B-basis Value	12.72	10.47		5.829
B-estimate			5.055	
A-estimate	11.68	9.431	3.957	5.233
Method	pooled	pooled	normal	normal

Table 4-15: Statistics and Basis Values for DNS Strength data

4.9 Quasi Isotropic Double Notched Shear (DNS1)

The DNS1 Shear data is not normalized. Data is available for only one property, strength. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition.

The RTA dataset failed the Anderson Darling k-sample test (ADK test) for batch but batch D

As-measured			
Env	RTA	ETA	ETW
Mean	10.17	5.989	5.783
Stdev	0.6216	0.1632	0.3767
CV	6.113	2.726	6.515
Mod CV	7.056	8.000	7.258
Min	8.905	5.760	5.255
Max	11.04	6.249	6.356
No. Batches	3	1	3
No. Spec.	18	6	18
Basis Values and Estimates			
B-basis Value			5.039
B-estimate	6.461	5.495	
A-estimate	3.814	5.143	4.512
Method	ANOVA	Normal	Normal
Modified CV Basis Values and Estimates			
B-basis Value	NA		4.954
B-estimate		4.546	
A-estimate		3.558	4.368
Method		normal	normal

4.10 Quasi Isotropic Unnotched Tension (UNT1)

The UNT1 data is normalized, so statistics for both as measured and normalized are provided.

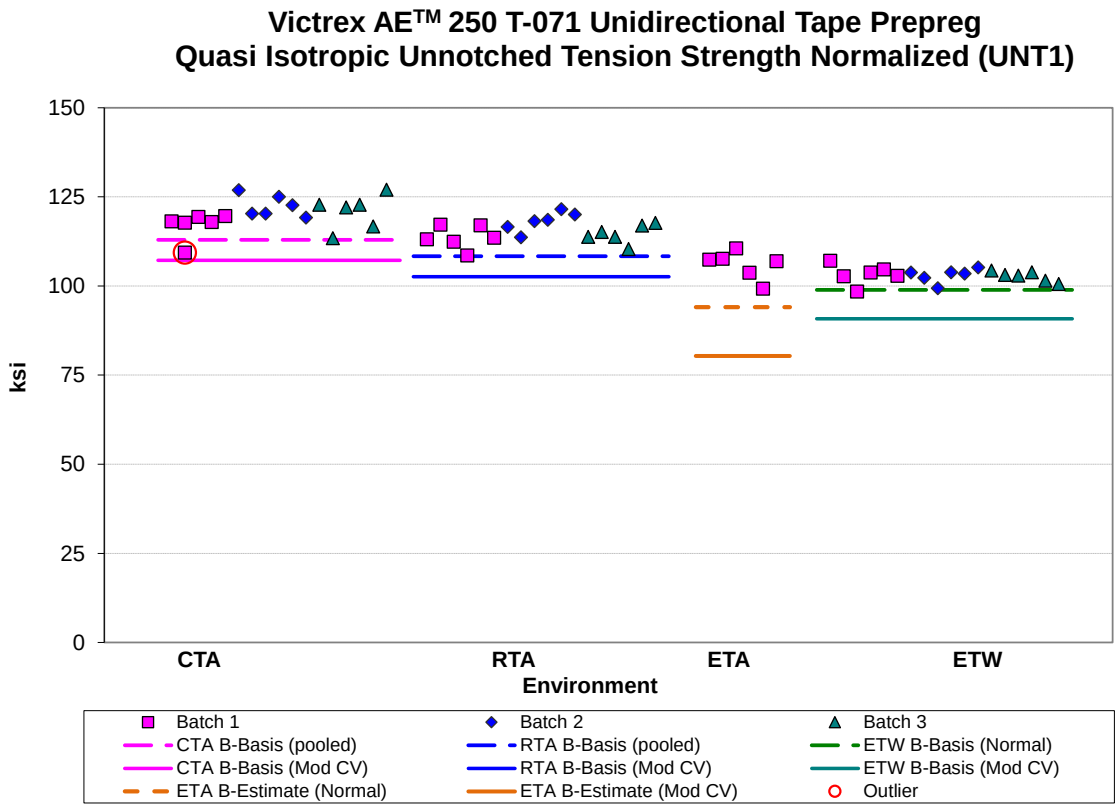

Figure 4-10: Batch Plot for UNT1 strength normalized

Env	CTA	RTA	ETA	ETW	CTA	RTA	ETA	ETW
Mean	120.1	115.4	105.9	103.0	120.5	114.4	103.4	103.2
Stdev	4.405	3.340	3.917	2.055	5.855	4.359	2.898	2.702
CV	3.669	2.893	3.699	1.995	4.861	3.810	2.802	2.617
Modified CV	6.000	6.000	8.000	6.000	6.430	6.000	8.000	6.000
Min	109.4	108.6	99.24	98.44	106.3	105.7	98.18	95.42
Max	127.0	121.5	110.5	107.1	130.1	121.2	106.3	107.2
No. Batches	3	3	1	3	3	3	1	3
No. Spec.	18	18	6	18	18	18	6	18
B-basis Value	112.9	108.3		98.93				97.61
B-estimate			94.04		90.75	89.44	94.65	
A-estimate	108.1	103.5	85.60	96.05	69.57	71.62	88.41	91.52
Method	pooled	pooled	Normal	Normal	ANOVA	ANOVA	Normal	Weibull
B-basis Value	107.2	102.6		90.79	107.1	101.1		91.01
B-estimate			80.38				78.50	
A-estimate	98.43	93.81	62.92	82.16	98.05	92.01	61.45	82.36
Method	pooled	pooled		pooled	nal	Nor430ed	n	6.000

Unnotched Tension (UNT1) Modulus Statistics								
	Normalized				As-measured			
Env	CTA	RTA	ETA	ETW	CTA	RTA	ETA	ETW
Mean	7.067	7.259	6.654	6.486	7.087	7.194	6.500	6.504
Stdev	0.2154	0.2178	0.08937	0.1466	0.2348	0.2843	0.04481	0.2468
CV	3.048	3.001	1.343	2.260	3.314	3.951	0.6894	3.794
Modified CV	6.000	6.000	8.000	6.000	6.000	6.000	8.000	6.000
Min	6.361	6.969	6.532	6.198	6.440	6.758	6.458	6.008
Max	7.361	7.757	6.744	6.682	7.458	7.717	6.587	6.811
No. Batches	3	3	1	3	3	3	1	3
No. Spec.	18	18	6	18	18	18	6	18

Table 4-18

4.11 “Soft” Unnotch 4.11

Env **CTA**

4.12 "Hard" Unnotched Tension 3 (UNT3)

The UNT3 data is normalized, so statistics for both as-measured and normalized are provided. Data is available for two properties, strength and modulus.

The as-measured CTA, RTA and ETW datasets and the normalized RTA datasets failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When the four datasets were transformed according to the assumptions of the modified CV method, they all passed the ADK test, so the modified CV basis values are provided. All three conditions met all requirements for pooling after the modified CV transformation of the data for both the normalized and the as-measured datasets.

The normalized ETW dataset failed all distribution tests (Normal, Lognormal and Weibull) and required the non-parametric method to compute basis values. After this dataset was transformed according to the assumptions of the modified CV method, it had an adequate fit to the normal distribution, so modified CV basis values are provided.

There was one statistical outlier. The lowest value in batch two of the normalized RTA dataset was an outlier for batch two only. It was not an outlier for the RTA condition or in the as-measured dataset. It was retained for this analysis.

Statistics and basis values are given for UNT3 strength data in Table 4-21 and for the modulus data in Table 4-22. The normalized data and the basis values are shown graphically in Figure 4-12.

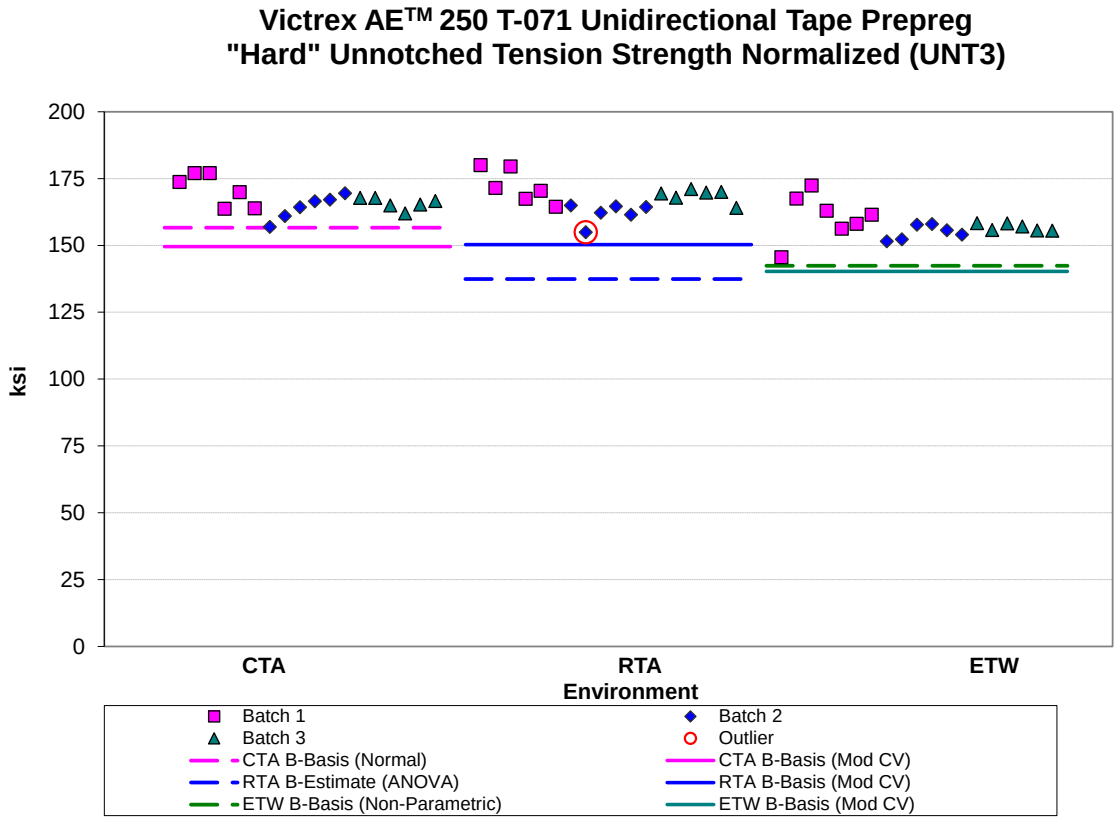

Figure 4-12: Batch Plot for UNT3 strength normalized

5262659

4.13 Unnotched Compression 900 (UNC0)

The UNC0 data is normalized, so statistics for both as-measured and normalized are provided. Data is available for two properties, strength and modulus. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition.

The CTA and RTA conditions met all requirements for pooling. The ETW datasets, both normalized and as-measured, failed normality and the Weibull distribution provided the best fit for the dataset. The as-measured ETW dataset passed the normality test applying the modified CV transformation to the data, so modified CV basis values could be computed for the as-measured ETW condition. However, the normalized ETW did not pass normality so no modified CV basis values were computed.

There are three outliers. The largest value in batch two of the as-measured RTA dataset is an outlier for batch two only, but not for the RTA condition and not for the normalized dataset. The lowest value in batch three of the as-measured RTA dataset is an outlier for the RTA condition, but not for batch three only and not for the normalized dataset. The lowest value in batch three of the ETW dataset is an outlier for batch three (both normalized and as-measured datasets) and for the ETW condition for the as-measured dataset but not for the normalized dataset. All three outliers were retained for this analysis.

Statistics and estimates of basis values are given for strength data in Table 4-23 and for the modulus data in Table 4-24. The normalized data and the estimates are shown graphically in Figure 4-13.

Unnotched Compression (UNC0) Modulus Statistics								
	Normalized				As-measured			
Env	CTA	RTA	ETA	ETW	CTA	RTA	ETA	ETW
Mean	9.386	9.514	9.217	8.991	9.294	9.451	9.220	8.976
Stdev	0.1777	0.1449	0.05857	0.1037	0.2976	0.1417	0.08394	0.1531
CV	1.893	1.523	0.6355	1.153	3.202	1.500	0.9104	1.706
Mod CV	6.000	6.000	8.000	6.000	6.000	6.000	8.000	6.000
Min	9.058	9.286	9.129	8.768	8.879	9.201	9.125	8.684
Max	9.770	9.807	9.284	9.194	9.980	9.699	9.354	9.258
No. Batches	3	3	1	3	3	3	1	3
No. Spec.	18	18	6	18	18	18	6	18

4.14 Quasi Isotropic Unnotched Compression 1 (UNC1)

The UNC1 data is normalized, so statistics for both measured and normalized are provided. Data is available for two properties, strength and modulus. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition.

Both as measured and the normalized RTA datasets failed the Anderson-Darling

Env	RTA	ETA	ETW2	ETW	RTA	ETA	ETW2	ETW
Mean	81.36	65.99	66.56	61.08	81.89	67.67	67.76	62.60
Stdev	3.078	2.284	2.212	3.221	3.048	2.930	2.527	3.676
CV	3.784	3.461	3.323	5.273	3.722	4.329	3.730	5.872

4.15 “Soft” Unnotched Compression 2 (UNC2)

The UNC2 data is normalized, so statistics for both measured and normalized are provided. Data is available for two properties, strength and modulus.

The as-measured RTA dataset failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH 17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When the dataset was transformed according to the assumptions of the modified CV method, it passed the ADK test, so the modified CV basis values are provided.

There were no statistical outliers.

Statistics and basis values are given for UNC2 strength data in Table 4-27 and for the modulus data in Table 4-28. The normalized data and the basis values are shown graphically in Figure 4-15.

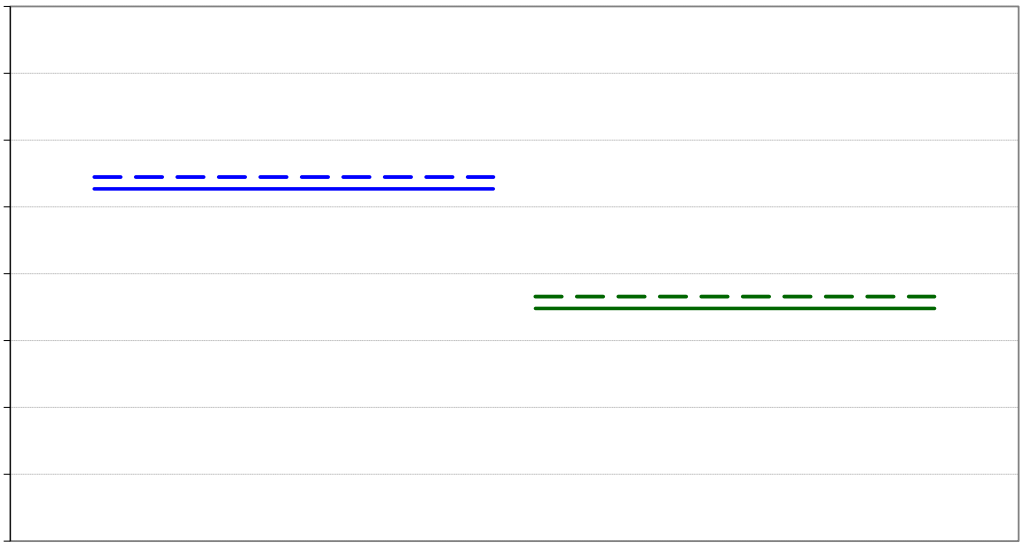

Env	RTA	ETW	RTA	ETW
Mean	58.36	40.48	58.70	40.80
Stdev	2.219	2.042	3.050	2.428
CV	3.802	5.043	5.196	5.951
Modified CV	6.000	6.522	6.598	6.976
Min	53.22	35.50	51.50	34.55
Max	62.10	43.50	63.55	44.43
No. Batches	3	3	3	3
No. Spec.	18			

4.16 “Hard” Unnotched Compression 3 (UNC3)

The UNC3 data is normalized, so statistics for both as

Unnotched Compression (UNC3) Strength Basis Values				
	Normalized		As-measured	
Env	RTA	ETW	RTA	ETW
Mean	108.8	75.14	111.6	76.93
Stdev	3.197	3.850	3.759	4.931
CV	2.938	5.125	3.367	6.410
Modified CV	6.000	6.562	6.000	7.205
Min	102.5	66.68	102.6	66.18
Max	113.9	80.91	118.0	83.18
No. Batches	3	3	3	3
No. Spec.	18	18	18	18
Basis Values and Estimates				
B-basis Value	102.3	68.69	104.2	
B-estimate				53.54
A-estimate	97.96	64.31	98.97	36.87
Method	pooled	pooled	Normal	ANOVA
Modified CV Basis Values and Estimates				
B-basis Value	98.25	64.60	100.4	65.73
A-estimate	91.09	57.43	92.83	58.11
Method	pooled	pooled	pooled	pooled

4.17 Quasi Isotropic Open-Hole Tension 1 (OHT1)

The OHT1 data is normalized, so statistics for both as-measured and normalized are provided. Data is available for only one property, strength. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition.

The CTA and RTA conditions could be pooled for the normalized data.

The as-measured CTA and both the normalized and as-measured ETW datasets failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When the three datasets were transformed ade4 (i)-2 (ng)]TJ -23.855 -1.15 Td [(t)-2 (he)-1 (A)2 (N)2 ((he)Td [(

Env	CTA	RTA	ETW	CTA	RTA	ETW
Mean	47.85	44.02	32.73	48.08	43.64	33.16
Stdev	2.145	1.834	0.4707	1.808	1.385	0.5832
CV	4.482	4.166	1.438	3.760	3.174	1.759
Modified CV	6.241	6.083	6.000	6.000	6.000	6.000
Min	44.66	41.28	31.86	45.57	41.12	31.99
Max	52.02	47.72	33.73	51.51	46.34	34.05
No. Batches	3	3	3	3	3	3
No. Spec.	18	18	18	18	18	18
B-basis Value			31.80			32.00
B-estimate	36.67	33.54		39.96	36.53	
A-estimate	28.70	26.07	31.14	34.17	31.46	31.19
Method	ANOVA	ANOVA	Normal	ANOVA	ANOVA	Normal
B-basis Value	43.28	39.46	28.17	43.61	39.17	28.68
A-estimate	40.24	36.41	25.12	40.62	36.19	25.70
Method	pooled	pooled	pooled	pooled	pooled	pooled

4.19 “Hard” Open-Hole Tension3 (OHT3)

The OHT3 data is normalized, so statistics for both measured and normalized are provided.
Data is available for only one property, strength.

All six datasets failed the Anderson Darling sample test to normality (α = 0.05).

4.20 Quasi Isotropic Open-Hole Compression 1 (OHC1)

The OHC1 data is normalized, so statistics for both as-measured and normalized are provided. Data is available for only one property, strength. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition.

The normalized and as-measured RTA datasetst

4.21 “Soft” Open-Hole Compression 2 (OHC2)

The OHC2 data is normalized, so statistics for both measured and normalized are provided. Data is available for only one property, strength.

The normalized and measured RTA datasets and the measured ETW dataset failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When these datasets were transformed according to the assumptions of the modified CV method, they passed the ADK test, so the modified CV basis values are provided. Pooling was acceptable for the normalized modified CV basis value computations but the measured datasets failed Levene’s test after the modified CV transformation of the data. Data could not be pooled.

There was one outlier. The lowest value in batch two of both the normalized and measured ETW datasets was an outlier for batch two but not the ETW condition. It was retained for this

4.22 “Hard” Open- Hole Compression 3 (OHC3)

The OHC3 data is normalized, so statistics for both measured and normalized are provided. Data is available for only one property, strength.

All four datasets failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When the normalized datasets were transformed according to the assumptions of the modified CV method, they both passed the ADK test, the as-measured datasets did not. Modified CV basis values are provided for the normalized datasets but pooling was not acceptable due to failure of Levene’s test for equality of variance.

There were no statistical outliers.

Statistics, estimates and basis values are given for OHC3 strength data in Table 4.36. The normalized data and the basis values are shown graphically in Figure 4.22.

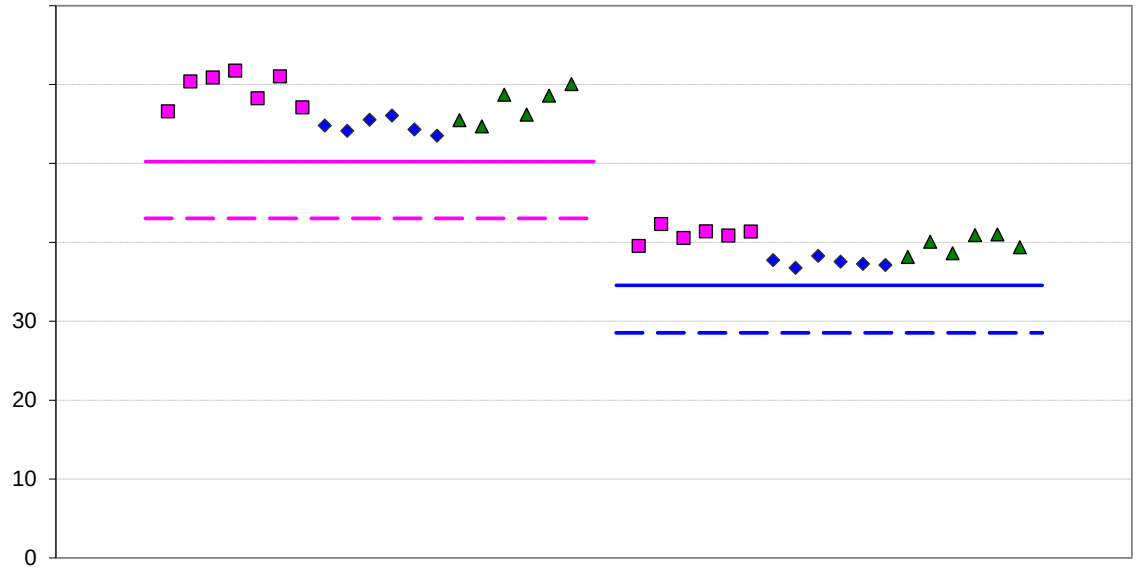

Env	RTA	ETW	RTA	ETW
Mean	57.27	39.39		

4.23 Quasi Isotropic Filled-Hole Tension1 (FHT1)

The FHT1 data is normalized, so statistics for both measured and normalized are provided. Data is available for only one property, strength. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition.

Pooling was acceptable for the CTA and RTA conditions for both normalized and measured datasets. The ETA and ETW conditions could not pooled due to insufficient specimens in the ETA condition.

The normalized ETW dataset failed all distribution tests (Normal, Lognormal and Weibull) and required the non-parametric method to compute basis values. After this dataset was transformed according to the assumptions of the modified CV method, it still failed to the normal distribution, so modified CV basis values could not be provided for that dataset. 13/P

Env	CTA	RTA	ETA	ETW	CTA	RTA	ETA	ETW
Mean	64.13	59.65	55.73	54.65	64.87	60.25	57.11	55.39
Stdev	1.339	1.121	1.544	1.0183	1.498	1.131	1.334	1.228
CV	2.088	1.879	2.770	1.863	2.309	1.877	2.336	2.217
Modified CV	6.000	6.000	8.000	6.000	6.000	6.000	8.000	6.000
Min	61.61	57.43	52.99	53.35	61.42	58.39	54.86	53.19
Max	66.37	62.06	57.09	55.96	67.09	62.80	58.18	57.28
No. Batches	3	3	1	3	3	3	1	3
No. Spec.	18	18	6	18	18	18	6	18
B-basis Value	61.88	57.40		53.02	62.45	57.83		52.97
B-estimate			51.05				53.06	
A-estimate	60.35	55.87	47.72	49.67	60.81	56.19	50.19	51.25
Method	p0.7 (d)]TJ	8..9	1.6	Bas				

4.24 “Soft” Filled-Hole Tension2 (FHT2)

The FHT2 data is normalized, so statistics for both measured and normalized are provided. Data is available for only one property, strength.

The normalized RTA dataset failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH 17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. When the normalized dataset was transformed according to the assumptions of the modified CV method, it passed the ADK test. All three normalized datasets could be pooled to compute the modified CV basis values.

The three as-measured datasets could not be pooled due to a failure of Levene’s test, but the RTA and ETW conditions met all requirements for pooling. After the datasets were transformed according to the assumptions of the modified CV method, they passed Levene’s test and could be pooled to compute the modified CV basis values.

There were no statistical outliers.

Statistics and basis values are given for FHT2 strength data in Table 4-38. The normalized data and the B-basis values are shown graphically in Figure 4-24.

[redacted]

Filled-Hole Tension (FHT2) Strength Basis Values and Statistics						
	Normalized			As-measured		
Env	CTA	RTA	ETW	CTA	RTA	ETW
Mean	53.66	47.09	35.24	54.02	46.99	35.50
Stdev	2.420	1.282	0.7180	2.234	1.114	0.8008
CV	4.510	2.723	2.037	4.135	2.372	2.256
Modified CV	6.255	6.000	6.000	6.068	6.000	6.000
Min	47.78	45.49	34.39	48.62	45.64	34.09
Max	57.08	49.27	36.54	57.41	49.20	37.23
No. Batches	3	3	3	3	3	3
No. Spec.	18	18	18	18	18	18
Basis Values and Estimates						
B-basis Value	48.88		33.83	49.61	45.22	33.73
B-estimate		40.57				
A-estimate	45.50	35.92	32.82	46.48	44.02	32.53
Method	Normal	ANOVA	Normal	Normal	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	48.68	42.11	30.26	49.09	42.06	30.57
A-estimate	45.36	38.79	26.94	45.81	38.77	27.29
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-38: Statistics and Basis Values for FHT2 Strength data

4.25 “Hard” Filled-Hole Tension3 (FHT3)

The FHT3 data is normalized, so statistics for both measured and normalized are provided. Data is available for only one property, strength.

Env	CTA	RTA	ETW	CTA	RTA	ETW
Mean	83.79	79.85	75.23	85.82	80.91	77.14
Stdev	3.909	3.101	2.949	3.652	2.936	2.639
CV	4.665	3.884	3.920	4.255	3.629	3.421
Modified CV	6.332	6.000	6.000	6.127	6.000	6.000
Min	79.15	74.71	70.99	81.37	76.59	73.33
Max	90.34	83.98	80.01	91.90	84.94	81.37
No. Batches	3	3	3	3	3	3
No. Spec.	18	18	18	18	18	18
B-estimate	56.91	59.04	55.45	61.46	62.03	61.03
A-estimate	37.71	44.18	41.33	44.07	48.55	49.54
Method	ANOVA	ANOVA	ANOVA	ANOVA	ANOVA	ANOVA

38w -35.94A-estima87.7133 ANOV-358.3972 -0Tw 93 -lMet3A

#01 Statistic Comparison (EHC1) for FWC2182 0 Td [59.4 (Tc) Td [30.3 ([d 0 Tc3

	Normalized			As-measured		
Env	RTA	ETA	ETW	RTA	ETA	ETW
Mean	74.84	56.91	51.45	75.41	57.90	52.20
Stdev	2.511	1.126	1.632	2.539	1.092	1.784
CV	3.354	1.979	3.172	3.367	1.885	3.418
Modified CV	6.000	8.000	6.000	6.000	8.000	6.000
Min	69.60	55.43	48.10	69.35	56.65	48.94
Max	80.12	58.44	53.55	80.86	59.54	54.75
No. Batches	3	1	3	3	1	3
No. Spec.	18	6	18	18	6	18
B-basis Value	69.89		48.23	70.40		48.68
B-estimate		53.50			54.59	
A-estimate	66.37	51.07	45.95	66.85	52.24	46.18
Method	Normal	Normal	Normal	Normal	Normal	Normal
B-basis Value	65.98		45.36	66.48		46.02
B-estimate		43.19			43.95	
A-estimate	59.71	33.81	41.05	60.16	34.40	41.64
Method	Normal	Normal	Normal	Normal	Normal	Normal

4.27 "Soft" Filled-Hole Compression 2 (FHC2)

The FHC2 data is normalized, so statistics for both measured and normalized are provided. Data is available for only one property, strength.

Both the normalized and as-measured RTA datasets failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. Where datasets were transformed according to the assumptions of

Filled-Hole Compression (FHC2) Strength Basis Values and Statistics				
	Normalized		As-measured	
Env	RTA	ETW	RTA	ETW
Mean	57.09	37.75	57.04	37.90
Stdev	1.785	1.813	1.963	1.602
CV	3.126	4.802	3.442	4.227
Modified CV	6.000	6.401	6.000	6.113
Min	52.60	35.10	52.94	35.42
Max	59.75	40.64	59.64	40.78
No. Batches	3	3	3	3
No. Spec.	18	18	18	18
Basis Values and Estimates				
B-basis Value		34.17		34.73
B-estimate	48.18		45.25	
A-estimate	41.83	31.63	36.83	32.49
Method	ANOVA	Normal	ANOVA	Normal
Modified CV Basis Values and Estimates				
B-basis Value	51.69	32.35	51.72	32.57
A-estimate	48.02	28.68	48.10	28.95
Method	pooled	pooled	pooled	pooled

	Env	RTA	ETW	RTA	ETW
. Tc 0	Mean	915.455	94	5.54	

4.29 Quasi Isotropic Single-Shear Bearing 1 (SSB1)

The SSB1 data is normalized, so statistics for both measured and normalized are provided. The ETA dataset lacked sufficient specimens to meet CMH-17 guidelines, so only estimates are provided for that condition. Data was available for three properties: Initial Peak Strength, 2% Offset Strength and Ultimate Strength. There was insufficient data to compute basis values and estimate for the Initial Peak property, so design values were computed for the 2% Offset Strength and Ultimate Strength properties only.

The normalized and as-measured ETW datasets for the 2% Offset Strength failed all distribution tests (Normal, Lognormal and Weibull) and required the non-parametric method to compute basis values. After these datasets were transformed according to the assumptions of the modified CV method, the normalized ETW dataset had an adequate fit to the normal distribution while the as-measured ETW dataset did not. So modified CV basis values are not provided for the as-measured ETW dataset.

The normalized ETW dataset for Ultimate Strength did not pass the normality test. The lognormal distribution provided an adequate fit to the dataset, so that distribution was used to compute basis values and estimates. After this dataset was transformed according to the assumptions of the modified CV method, it had an adequate fit to the normal distribution so modified CV basis values were provided.

There were two statistical outliers. The largest value in batch one of the ETW dataset was an outlier for the 2% Offset Strength property. It was an outlier for both the normalized- and as-measured datasets and for batch one of the as-measured dataset and the ETW condition for both datasets. It was not an outlier for the Ultimate Strength property. The largest value in batch three of the ETW dataset was an outlier for both the 2% Offset Strength and the Ultimate Strength properties. It was an outlier for both the normalized and as-measured datasets and for both batch one only. Both outliers were retained for this analysis.

Statistics, estimates and basis values are given for SSB1 2% Offset Strength data in Table 4-43 and for the Ultimate Strength data in Table 4-44. The normalized data and the basis values are shown graphically in for the 2% Offset Strength in Figure 4-29 and for the Ultimate Strength in Figure 4-30.

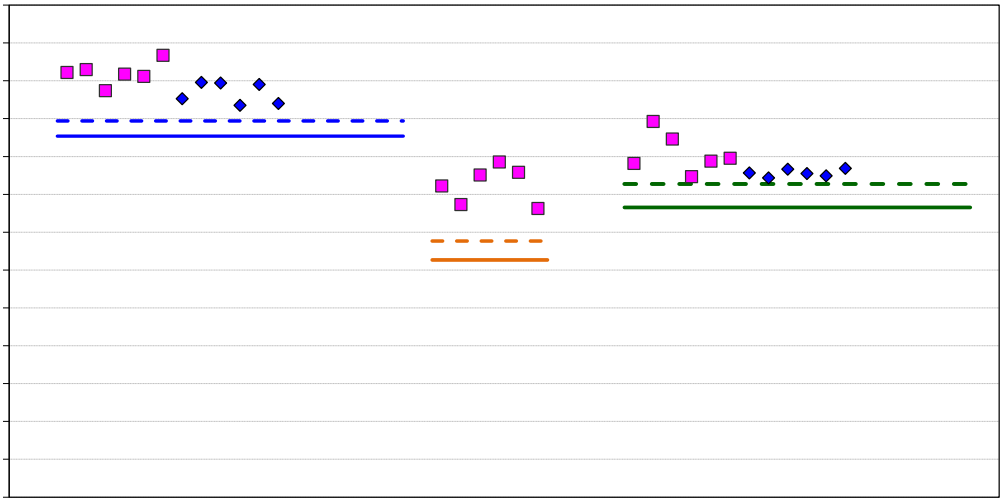

Single Shear Bearing (SSB1) 2% Offset Strength Basis Values and Statistics						
	Normalized			As-measured		
Env	RTA	ETA	ETW	RTA	ETA	ETW
Mean	108.5	82.55	87.69	108.2	82.58	88.47
Stdev	4.620	4.920	4.270	3.965	4.737	3.446
CV	4.258	5.961	4.870	3.666	5.736	3.895
Modified CV	6.129	8.000	6.435	6.000	8.000	6.000
Min	101.3	76.25	83.61	100.1	75.87	84.54
Max	116.7	88.58	99.26	114.0	88.52	97.88
No. Batches	3	1	3	3	1	3
No. Spec.	18	6	18	18	6	18
Basis Values and Estimates						
B-basis Value	99.39		82.75	100.3		83.41
B-estimate		67.64			68.23	
A-estimate	92.92	57.05	64.67	94.78	58.03	67.89
Method	Normal	Normal	Non-Parametric	Normal	Normal	Non-Parametric
Modified CV Basis Values and Estimates						
B-basis Value	95.38		76.55	95.34		NA
B-estimate		62.65			62.68	
A-estimate	86.09	49.04	68.67	86.28	49.06	
Method	Normal	Normal	Normal	Normal	Normal	

Table 4-43: Statistics and Basis Values for SSB1 2% Offset Strength data

4.30 "Soft" Single-Shear Bearing 2 (SSB2)

The SSB2 data is normalized, so statistics for both measured and normalized data are provided. Data was available for two properties, 2% Offset Strength and Ultimate Strength.

While the RTA condition did not pass the normality test, the RTA and ETW conditions passed the normality test for the pooled dataset and pooling was appropriate for both 2% Offset Strength and Ultimate Strength for both the normalized and measured datasets.

There were two statistical outliers. The largest value in batch three of the RTA condition for the normalized 2% Offset Strength property was an outlier for batch three only. It was not an outlier for the RTA condition or in the as-measured dataset or for the Ultimate Strength property. The lowest value in batch one of the RTA condition for the Ultimate Strength property was an outlier for batch one only, not for the RTA condition. It was an outlier for both the normalized and as-measured datasets. It was not an outlier for the 2% Offset Strength property. Both outliers were retained for this analysis.

Statistics, estimates and basis values are given for the SSB2 2% offset strength data in 2% 4-31 s

Single Shear Bearing (SSB2) Strength Basis Values and Statistics								
	2% Offset Strength				Ultimate Strength			
	Normalized		As-measured		Normalized		As-measured	
Env	RTA	ETW	RTA	ETW	RTA	ETW	RTA	ETW
Mean	110.0	84.52	110.8	86.50	132.7	92.81	133.7	94.99
Stdev	3.038	3.723	2.901	3.583	3.246	2.946	3.295	2.598
CV	2.763	4.405	2.617	4.142	2.446	3.174	2.464	2.736
Modified CV	6.000	6.202	6.000	6.071	6.000	6.000	6.000	6.000
Min	104.9	75.71	106.3	78.60	127.0	86.82	127.9	90.01
Max	115.6	90.28	116.6	93.07	136.8	98.13	139.3	99.67
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	18	18	18	18	18	18	18	18
Basis Values and Estimates								
B-basis Value	103.8	78.33	104.9	80.56	127.0	87.16	128.3	89.58
A-estimate	99.56	74.12	100.8	76.52	123.2	83.32	124.7	85.90
Method	pooled	pooled	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates								
B-basis Value	99.11	73.66	99.91	75.59	120.2	80.29	121.1	82.31
A-estimate	91.72	66.28	92.49	68.16	111.7	71.78	112.4	73.69
Method	pooled	pooled	pooled	pooled	pooled	pooled	pooled	pooled

4.31 "Hard" Single-Shear Bearing 3 (SSB3)

The SSB3 data is normalized, so statistics for both measured and normalized are provided. Data was available for three properties: Initial Peak Strength, 2% Offset Strength and Ultimate Strength. There was insufficient data to compute basis values and estimate for Initial Peak, so design values were computed for the 2% Offset Strength and Ultimate Strength properties only.

The normalized and as-measured 2% offset datasets failed Levene's test and could not be pooled. When these datasets were transformed according to the assumptions of the modified CV method, they passed Levene's test and the pooled dataset passed normality. They could be pooled to "

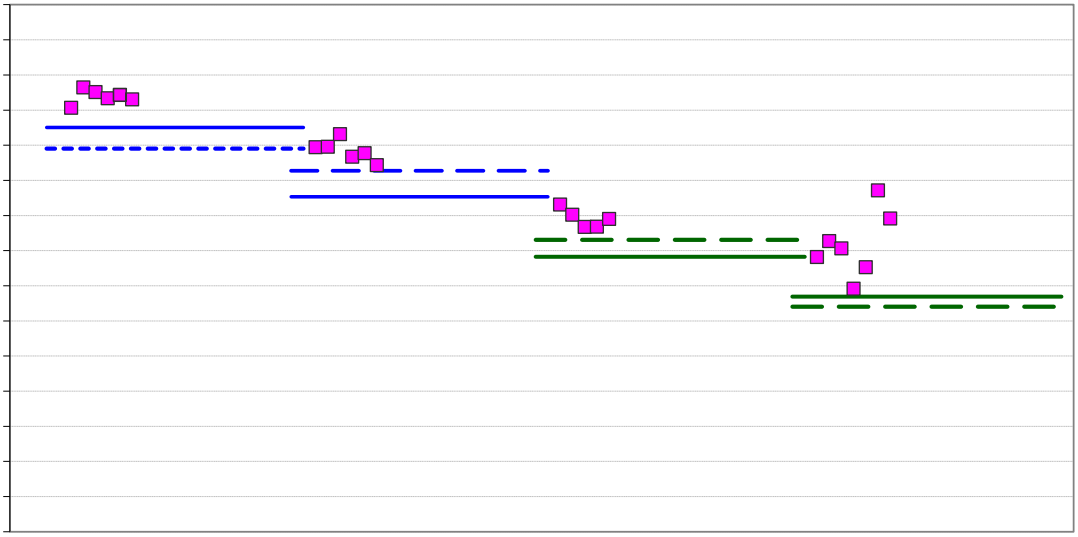

4.32 Quasi Isotropic Compression After Impact 1 (CAI 1)

Basis values are not computed for this property. Data from only one batch of material is available. However the summary statistics are presented in Table 4.47 and the data are displayed graphically in Figure 4.33.

5. Outliers

Outliers were identified according to the standards documented in section 2.1.5, which are in accordance with the guidelines developed in section 8.3.3 of CMH-17-1G. An outlier may be an outlier in the normalized data, the measured data, or both. A specimen may be an outlier for the batch only (before pooling the three batches within a condition together) or for the condition (after pooling the three batches within a condition together) or both.

Approximately 5 out of 100 specimens will be identified as outliers due to the expected random variation of the data. This test is used only to identify specimens to be investigated for a cause of the extreme observation. Outliers that have an identifiable cause are removed from the dataset as they inject bias into the computation of statistics and basis values. Specimens that are outliers for the condition and in both the normalized and measured data are typically more extreme and more likely to have a specific cause and be removed from the dataset than other outliers. Specimens that are outliers only for the batch, but not the condition and specimens that are identified as outliers only for the normalized data or the

Test	Condition	Batch	Specimen Number	Normalized Strength	Strength As-measured	High/ Low	Batch Outlier	Condition Outlier
TC	CTA	1	TC-A-C1-CTA-1	NA	32.96	Low	No	Yes
TC	CTA	2	TC-B-C2-CTA-2	NA	36.98	Low	Yes	No
UNC0					114.1			
Backout LC					212.2			
UNC0					100.3			
Backout LC					186.6			
UNC0				72.83	70.98			
Backout LC				143.6	140.0			
IPS - 5% Strain	ETA	1	IPS-A-C1-ETA-2	NA	4.038	Low		
VNS - 0.2% Offset	ETW	3	VNS-C-C2-ETW-2	NA	2.479	High	Yes	Yes
VNS - 0.2% Offset					1.292			
VNS - 5% Strain					3.324			
VNS - 5% Strain	CTA	2	VNS-B-C2-CTA-1	NA	13.87	High	Yes	Yes
VNS1 - Ult. Str.	RTA	1	VNS1-A-C1-RTA-3	NA	50.19	High	Yes	No
CAI Strength	RTA	1	CAI1-A-C1-RTA-3	34.44	34.58	Low		
FHC1	RTA	2	FHC1-B-C2-RTA-3	69.60	69.35	Low	Yes	No
FHC2	RTA	2	FHC2-B-C2-RTA-3	55.17	55.84	Low	Yes	No
FHC2	RTA	1	FHC2-A-C1-RTA-1	52.60	Not an outlier	Low	Yes	No
FHC3	ETW	3	FHC3-C-C1-ETW-2	57.93	58.75	Low	Yes	No
FHT1	RTA	2	FHT1-B-C2-RTA-3	Not an outlier	58.88	Low	Yes	No
FHT3	RTA	3	FHT3-C-C1-RTA-1	79.58	81.29	High	Yes	No
OHC1	ETW	3	OHC1-C-C1-ETW-3	33.69	34.39	High	Yes	Rut283.5sYe4

33.69

6. References

1. Snedecor, G.W. and Cochran, W.G., *Statistical Methods*, 7th ed., The Iowa State University Press, 1980, pp. 252-253.
2.