Approaches to Safe Nanotechnology

Ma a H a Sa C
A a E Na a

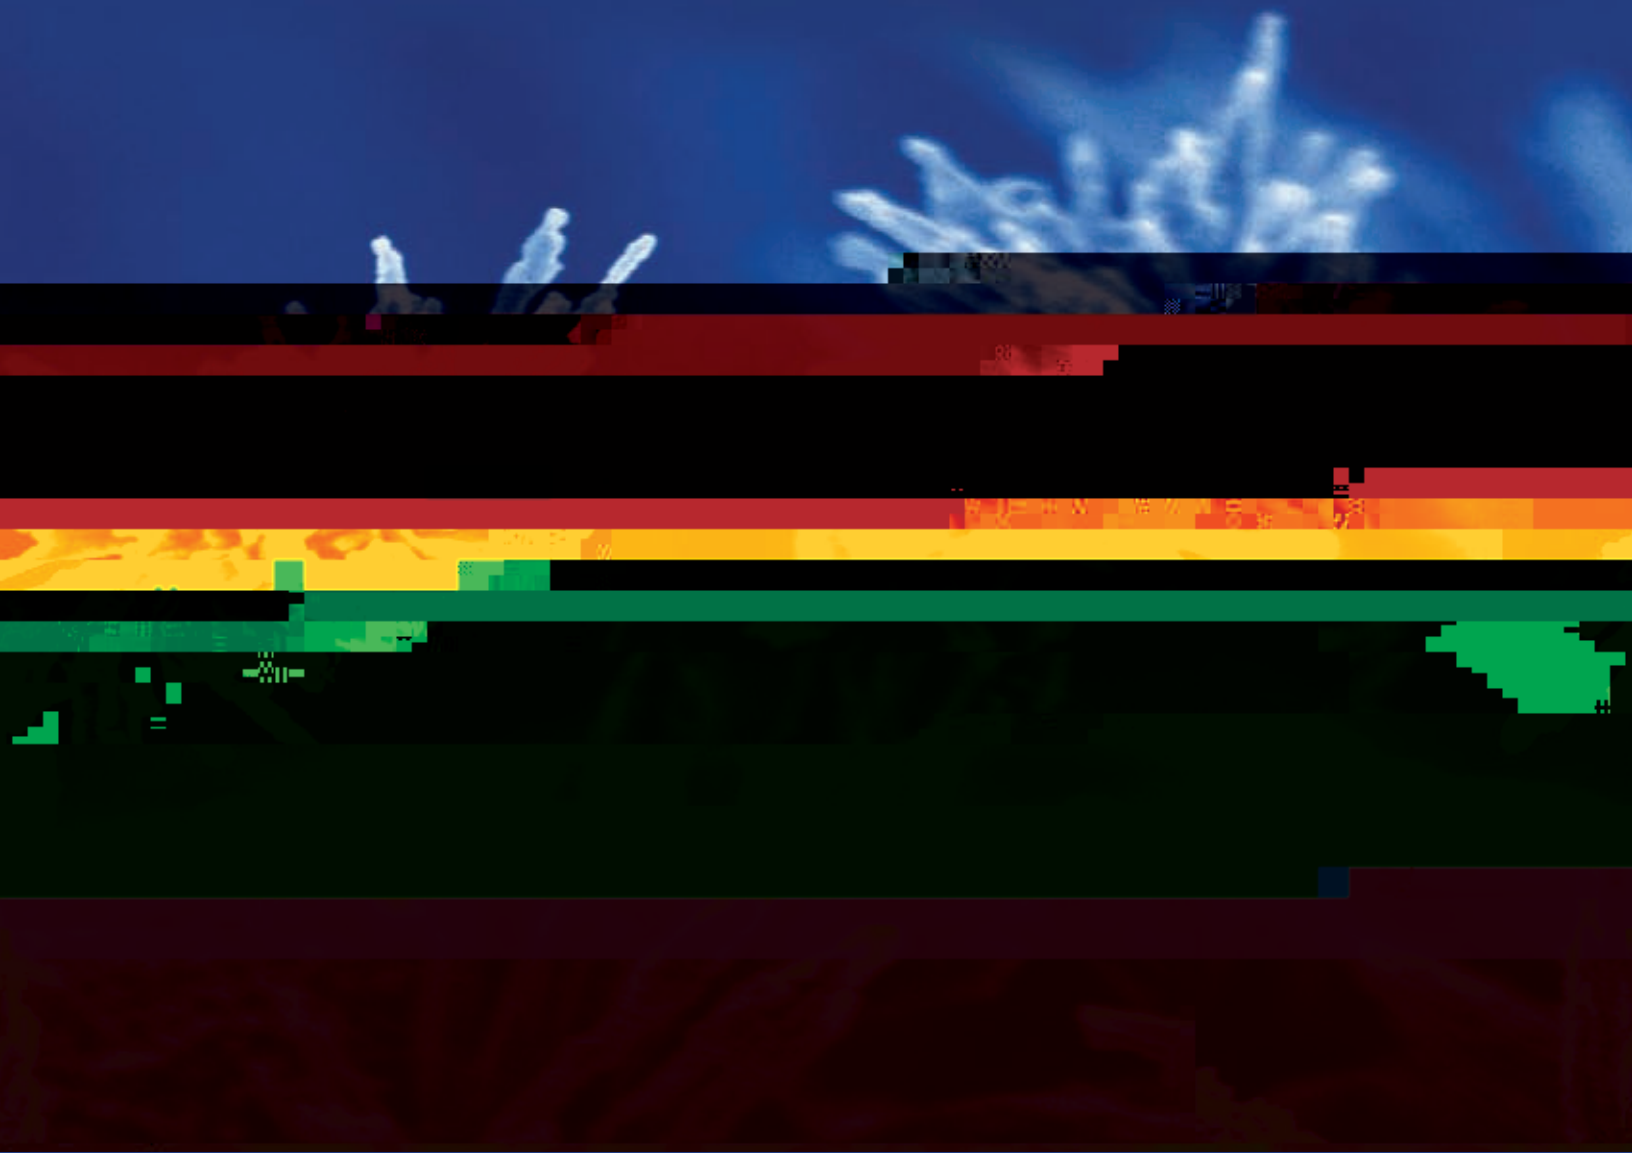

DEPARTMENT OF HEALTH AND HUMAN SERVICES
Centers for Disease Control and Prevention
National Institute for Occupational Safety and Health

Photo Credits:
Nanotrees, Ghim Wei Ho and Professor Mark Welland, Nanostructure Center, University of Cambridge

Nanotechnology has the potential to dramatically improve the effectiveness of a number of existing consumer and industrial products and could have a substantial impact on the development of new products in all sectors, ranging from disease diagnosis and treatment to environmental remediation. Because of the broad range of possible nanotechnology applications, continued evaluation of the potential health risks associated with exposure to nanomaterials is essential to ensure their safe handling. Engineered nanoparticles are materials purposefully produced with at least one dimension between 1 and 100 nanometers. Nanoparticles* often exhibit unique physical and chemical properties that impart specific characteristics essential in making engineered materials, but little is known about what effect these properties may have on human health. Research has shown that the physicochemical characteristics of particles can influence their effects in biological systems. These characteristics include particle size, shape, surface area, charge, chemical properties, solubility, oxidant generation potential, and degree of agglomeration. Until the results from research studies can fully elucidate the characteristics of nanoparticles that may pose a health risk, precautionary measures are warranted.

NIOSH has developed this document to provide an overview of what is known about the potential hazards of engineered

*In an attempt at standardization of terminology, the International Organization for Standardization-Technical Committee 229 has used the term nanomaterial to describe engineered 43(d)13(e)10(s)10(c)10(r)-1(].]TJEMC /Span <</MCID 13>>BDC 0 -c 0120 0 1 2 276.75 639Tm[(*ano)5(par)-17(t)-3(ic)5(les)]-349and)1-349aeas

  - Developing procedures for determining the need for and selecting proper personal protective equipment (e.g., clothing, gloves, respirators)
  - Systematically evaluating exposures to ensure that control measures are working properly and that workers are being provided the appropriate personal protective equipment

- Engineering control techniques such as source enclosure (i.e., isolating the generation source from the worker) and local exhaust ventilation systems should be effective for capturing airborne nanoparticles. Current knowledge indicates that a well-designed exhaust ventilation system with a high-efficiency particulate air (HEPA) filter should effectively remove nanomaterials.
- The use of good work practices can help to minimize worker exposures to nanomaterials. Examples of good practices include cleaning of work areas using HEPA vacuum pickup and wet wiping methods, preventing the consumption of food or beverages in workplaces where nanomaterials are handled, providing hand-washing facilities, and providing facilities for showering and changing clothes.

F v (. . . . . ‴
E \ S a . . . . . \
A v (. . . . . ‴
1

7.1.3 Surface-area measurements 28
7.1.4 Particle number concentration measurement 29
7.1.5 Surface-area estimation. 30
7.1.6 Particle number concentration mapping 31
7.2 Sampling Strategy. 32
8 G[illegible] W[illegible] E[illegible] Na[illegible]

1 Introduction

Nanotechnology is the manipulation of matter on a near-atomic scale to produce new structures, materials, and devices. This technology has the ability to transform many industries and can be applied in many ways to areas ranging from medicine to manufacturing. Research in nanoscale technologies is growing rapidly worldwide. Lux Research [2007] projects that new emerging nanotechnology applications will affect nearly every type of manufactured product through the middle of the next decade, becoming incorporated into 15% of global manufacturing output, totaling $2.6 trillion in 2014.

Nanomaterials present new challenges to understanding, predicting, and managing potential health risks to workers. As with any material being developed, scientific data on the health effects in exposed workers are largely unavailable. I [illegible]. Safety and health practitioners recognize the critical lack of specific guidance on the safe handling of nanomaterials—especially now, when the degree of risk to exposed workers is unknown. In the meantime, the extensive scientific literature on airborne particles—including toxicology and epidemiological studies, measurement techniques, and engineering controls—provides the best available data from which to develop interim approaches for working safely with nanomaterials and to develop hypotheses for studies of new nanomaterials.

The National Institute for Occupational Safety and Health (NIOSH) is working in parallel with the development and implementation of commercial nanotechnology through (*1*) conducting strategic planning and research, (*2*) partnering with public- and private-sector colleagues from the United States and abroad, and (*3*), making information widely available. The NIOSH goal is to provide national and world leadership for incorporating research findings about the implications and applications of nanotechnology into good occupational safety and health practice for the benefit of all nanotechnology workers. NIOSH has developed a strategic plan for coordinating nanotechnology research and for use as a guide for enhancing the development of new research efforts (www.cdc.gov/niosh/topics/nanotech/strat_plan.html).

2 Purpose

With the publication of this *Approaches to Safe Nanotechnology* document, NIOSH hopes to do the following:

- **Ra** a of the occupational safety and health issues being identified in the rapidly moving and changing science involving implications and applications of nanotechnology.
- **U** a on occupational safety and health practices in the production and use of nanomaterials (These recommendations will be updated as appropriate to reflect new information. They will address key components of occupational safety and health, including exposure monitoring, engineering controls, personal protective equipment, and administrative controls. They will draw from the ongoing NIOSH assessment of current best practices, technical knowledge, and professional judgment. Throughout the development of these guidelines, the utility of a hazard-based approach to risk assessment and control was evaluated and, where appropriate, recommendations are provided.)
- **Fa** a between NIOSH and its external partners from ongoing research, including success stories, applications, and case studies.
- **R** from industry, labor, academia, and other partners who are seeking science-based, authoritative guidelines.
- **I** where few or no data exist and where research is needed.

This document has been developed to provide a resource for stakeholders who wish to understand more about the safety and health implications and applications of nanotechnology in the workplace. The information and guidelines presented here are intended to aid in evaluating the potential hazard of exposure to engineered nanomaterials and to set the stage for the develop-

Nanotechnology involves the manipulation of matter at nanometer[†] scales to produce new materials, structures, and devices. The U.S. National Nanotechnology Initiative (see http://nano.gov/html/facts/whatIsNano.html) defines a technology as nanotechnology only if it involves all of the following:

- Research and technology development involving structures with at least one dimension in the range of 1–100 nanometers (nm), frequently with atomic/molecular precision
- Creating and using structures, devices, and systems that have unique properties and functions because of their nanoscale dimensions
- The ability to control or manipulate on the atomic scale

Nanotechnology is an enabling technology that offers the potential for unprecedented advances in many diverse fields. The ability to manipulate matter at the atomic or molecular scale makes it possible to form new materials, structures, and devices that exploit the unique physical and chemical properties associated with nanoscale structures. The promise of nanotechnology goes far beyond extending the use of current materials. New materials and devices with intricate and closely engineered structures will allow for (*1*) new directions in optics, electronics, and optoelectronics, (*2*) development of new medical imaging and treatment technologies, and (*3*) production of advanced materials with unique properties and high-efficiency energy storage and generation.

Although nanotechnology-based products are generally thought to be at the precompetitive stage, an increasing number of products and materials are becoming commercially available. These include nanoscale powders, solutions, and suspensions of nanoscale materials as well as composite materials and devices having a nanostructure. Nanoscale products and materials are increasingly used in optoelectronic, electronic, magnetic, medical imaging, drug delivery, cosmetic, catalytic, and materials applications. New nanotechnology consumer products are coming on the market at the rate of three to four per week, a finding based on the latest update to the nanotechnology consumer product inventory maintained by the Project on Emerging Nanotechnologies (PEN)[‡] (www.nanotechproject.org/inventories/consumer). The number of consumer products using nanotechnology has grown from 212 to 609 since PEN launched the world's first online inventory of manufacturer-identified nanotech goods in March 2006.

According to Lux Research [2007], in 2006, governments, corporations, and venture capitalists worldwide spent $11.8 billion on nanotechnology research and development (R&D), which was up 13% from 2005. By 2014, Lux

the Pth(Rw(iw04(tesnlatesw2).6s4(M)2(D)2( )$2f))10(h(Rs$2).6s4(M)2(D)2( )$2f) -14(1)]T1e22an3meh(Rwg10(s)11276

[†]1 nanometer (nm) = 1 billionth of a meter (10^{-9}).

F ı 4 1. Photomicrographs of airborne exposure to ultrafine (nanoscale) particles of welding fumes, diesel exhaust, and cerium oxide

will incorporate nanotechnology—or about 15% of total global output.

4.1 Nano-objects

The International Organization for Standardization Technical Committee 229 (Nanotechnologies) is developing globally recognized nomenclature and terminology for nanomaterials. According to ISO/TS 27687:2008, *nano-object* is defined as material with one, two, or three external dimensions in the size range from approximately 1–100 nm. Subcategories of nano-object are (*1*) *nanoplate*, a nano-object with one external dimension at the nanoscale; (*2*) *nanofiber*, a nano-object with two external dimensions at the nanoscale with a nanotube defined as a hollow nanofiber and a nanorod as a solid nanofiber; and (*3*) *nanoparticle*, a nano-object with all three external dimensions at the nanoscale. Nano-objects are commonly incorporated in a larger matrix or substrate referred to as a *nanomaterial*. Nano-objects may be suspended in a gas (as a nanoaerosol), suspended in a liquid (as a colloid or nanohydrosol), or embedded in a matrix (as a nanocomposite).

The precise definition of particle diameter depends on particle shape as well as how the diameter is measured. Particle morphologies may vary widely at the nanoscale. For instance, carbon fullerenes represent nano-objects with identical dimensions in all directions (i.e., spherical), whereas single-walled carbon nanotubes (SWCNTs) typically form convoluted, fiber-like nano-objects. Many regular but nonspherical particle morphologies can be engineered at the nanoscale, including flower- and belt-like structures. Please see www.nanoscience.gatech.edu/zlwang/research.html for examples of some nanoscale structures.

4.2 Ultrafine Particles

The term *ultrafine particle* has traditionally been used by the aerosol research and occupational and environmental health communities to describe airborne particles smaller than 100 nm in diameter. *Ultrafine* is frequently used in the context of nanometer-diameter particles that have not been intentionally produced but are the incidental products of processes involving combustion, welding, or diesel engines (see Figure 4–1). The term *nanoparticle* is frequently used with respect to particles demonstrating size-dependent physicochemical properties, particularly from a materials science perspective. T v a v

5 Potential Health Concerns

Na [illegible] a [illegible]. A [illegible] a [illegible] a [illegible] v [illegible] a [illegible] a [illegible] v [illegible] a [illegible] a [illegible] a) a [illegible] a [illegible] a [illegible]. These uncertainties arise because of gaps in knowledge about the factors that are essential for predicting health risks—factors such as routes of exposure, translocation of materials once they enter the body, and interaction of the materials with the body's biological systems. The potential health risk following exposure to a substance is generally associated with the magnitude and duration of the exposure, the persistence of the material in the body, the inherent toxicity of the material, and the susceptibility or health status of the person exposed. More data are needed on the health risks associated with exposure to engineered nanomaterials. Results of existing studies in animals and humans on exposure and response to ultrafine or other respirable particles provide a basis for preliminary estimates of the possible adverse health effects from exposures to similar engineered materials on a nanoscale. Experimental studies in rodents and cell cultures have shown that the toxicity of ultrafine or nanoparticles is greater than that of the same mass of larger particles of similar chemical composition [Oberdörster et al. 1992, 1994a, b; Lison et al. 1997; Tran et al. 1999, 2000; Brown et al. 2001; Barlow et al. 2005; Duffin et al. 2007]. In addition to particle surface area, other particle characteristics may influence toxicity, including surface functionalization or coatings, solubility, shape, and the ability to generate oxidant species and to adsorb biological proteins or bind to receptors [Duffin et al. 2002; Oberdörster et al. 2005a; Maynard and Kuempel 2005; Donaldson et al. 2006]. More research is needed on the influence of particle properties on interactions with biological systems and the potential for adverse effects. International research strategies for evaluating the safety of nanomaterials are actively being developed through cooperative efforts [Thomas et al. 2006].

Existing toxicity information about a given material of larger particle size can provide a baseline for anticipating the possible adverse health effects that may occur from exposure to a nanoscale material that has some of the same physicochemical properties (e.g., chemistry, density). However, predicting the toxicity of an engineered nanomaterial based on its physicochemical properties may not provide an adequate level of protection.

5.1 Exposure Routes

I [illegible] a [illegible] v [illegible] a [illegible]. The deposition of discrete nano-objects in the respiratory tract is determined by the particle's aerodynamic or thermodynamic diameter (i.e., the particle shape and size). Agglomerates of nano-objects will deposit according to the diameter of the agglomerate, not constituent nano-objects. Research is ongoing to determine the physical factors that contribute to the agglomeration and de-agglomeration of nano-objects in air, suspended in aqueous media, or once in contact with lung lining fluid and/or biological proteins. Evidence indicates

that the degree of agglomeration can affect the toxicity of inhaled nano-objects [Shvedova et al. 2007].

Discrete nanoparticles are deposited in the lungs to a greater extent than larger respirable particles [ICRP 1994], and deposition increases with exercise due to increase in breathing rate and change from nasal to mouth breathing [Jaques and Kim 2000; Daigle et al. 2003] and among persons with existing lung diseases or conditions (e.g., asthma, emphysema) [Brown et al. 2002]. Based on animal studies, discrete nanoparticles may enter the bloodstream from the lungs and translocate to other organs [Takenaka et al. 2001; Nemmar et al. 2002; Oberdörster et al. 2002].

Discrete nanoparticles (35–37-nm median diameter) that deposit in the nasal region may be able to enter the brain by translocation along the olfactory nerve, as was observed in rats [Oberdörster et al. 2004; Oberdörster et al. 2005a; Elder et al. 2006]. The transport of insoluble particles from 20–500 nm-diameter to the brain via sensory nerves (including olfactory and trigeminus) was reported in earlier studies in several animal models [De Lorenzo 1970; Adams and Bray 1983; Hunter and Dey 1998]. This exposure route for nanoparticles and to nanoscale biological agents has not been studied in humans.

Some studies suggest that nanomaterials could potentially enter the body through the skin during occupational exposure. Tinkle et al. [2003] have shown that particles smaller than 1 μm in diameter may penetrate into mechanically flexed skin samples. A more recent study reported that nanoparticles with varying physicochemical properties were able to penetrate the intact skin of pigs [Ryman-Rasmussen et al. 2006]. These nanoparticles were quantum dots of different size, shape, and surface coatings. They were reported to penetrate the stratum corenum barrier by passive diffusion and localize within the epidermal and dermal layers within 8–24 hours. The dosing solutions were 2- to 4-fold dilutions of quantum dots as commercially supplied and thus represent occupationally relevant doses.

At this time, it is not fully known whether skin penetration of nanoparticles would result in adverse effects in animal models. However, topical application of raw SWCNT to nude mice has been shown to cause dermal irritation [Murray et al. 2007]. Studies conducted in vitro using primary or cultured human skin cells have shown that both SWCNT and multi-walled carbon nanotubes (MWCNT) can enter cells and cause release of pro-inflammatory cytokines, oxidative stress, and decreased viability [Monteiro-Riviere et al. 2005; Shvedova et al. 2003]. It remains unclear, however, how these findings may be extrapolated to a potential occupational risk, given that additional data are not yet available for comparing the cell model studies with actual conditions of occupational exposure. Research on the dermal exposure of nanomaterials is ongoing (www.uni-leipzig.de/~nanoderm/).

Ingestion can occur from unintentional hand to mouth transfer of materials; this has been found to happen with traditional materials, and it is scientifically reasonable to assume that it also could happen during handling of nanomaterials. Ingestion may also accompany inhalation exposure because particles that are cleared from the respiratory tract via the mucociliary escalator may be swallowed [ICRP 1994]. Little is known about possible adverse effects from the ingestion of nanomaterials.

5.2 Effects Seen in Animal Studies

E [illegible]

toxicity is not known. Carbon nanotubes may contain metal catalysts as byproducts of their production, which could contribute to their

OSHA PEL for graphite (5 mg/m^3). Lam et al. [2004, 2006] provided similar estimates and suggested that the graphite PEL should not be used (e.g., on MSDS) as a safe concentration for workers exposed to CNTs. Compared

fullerene-treated group did not show these responses. Mesothelioma was considered by the authors as the primary cause of death, and constriction of the ileus due to severe peritoneal adhesion was considered to be the second major cause of death, suggesting that 3 mg/mouse exceeded the maximum tolerated dose of MWCNT. Whether mesotheliomia was a primary cause of death is somewhat speculative.

In a second study, Poland et al. [2008] administered to mice either MWCNT (two short and two long CNT samples), nanoscale carbon black, or amosite (short or long) at doses of 50 μg/mouse by intraperitoneal injection. The short CNTs were 10 nm or 15 nm in width, with no fibers larger than 15 μm in length detected; the long CNTs were 85 nm or 165 nm in width, and 24% or 84%, respectively, were larger than 15 μm in length (the percentage of fibers longer than 5 μm was not reported). After either 24 hours or 7 days, the long MWCNT caused inflammation and granulomatous lesions that were qualitatively and quantitatively similar to that caused by the long asbestos. The short, low-aspect-ratio, tangled aggregates of MWCNT did not produce these responses at the

et al. 2006; Ambroise et al. 2007; Bowler et al. 2007]. The implications of these studies to engineered nanomaterials, which may have different particle properties, are uncertain. Studies of airborne particles and fibers in the workplace do provide relevant background information about the particle-related lung diseases and mechanisms, and some limited quantitative estimates of exposures and risk of adverse health effects. As such, these studies provide a point of reference, including baseline information and estimates regarding possible health risks of exposure to other nanoscale particles depending on the extent to which the

There are currently no national or international consensus standards on measurement techniques for nanomaterials in the workplace.

with a known process (e.g., diesel exhaust particulate).

Aerosol samples can be collected using inhalable, thoracic, or respirable samplers, depending on the region of the respiratory

radioactive ions. For aerosols less than approximately 100 nm in size, measurement of the Fuchs surface area is probably a good indicator of external surface area (or geometric surface area). However, for aerosols greater than approximately 1 μm, the relationship with geometric particle surface area is lost [Fuchs 1964]. Measurements of active surface area are generally insensitive to particle porosity. The epiphaniometer is not well suited to widespread use in the workplace because of the inclusion of a radioactive source and the lack of effective temporal resolution.

This same measurement principle can be applied with the use of a portable aerosol diffusion charger. Studies have shown that these devices provide a good estimate of aerosol external surface area when airborne particles are smaller than 100 nm in diameter. For larger particles, diffusion chargers underestimate aerosol surface area. However, further research is needed to evaluate the degree of underestimation. Extensive field evaluations of commercial instruments are yet to be reported. However, laboratory evaluations with monodisperse silver particles have shown that two commercially available diffusion chargers can provide good measurement data on aerosol external surface area for particles smaller than 100 nm in diameter but underestimate the aerosol surface area for particles larger than 100 nm in diameter [Ku and Maynard 2005, 2006].

7.1.4 Particle number concentration measurement

Particle number concentration has been associated with adverse responses to air pollution in some human studies [Timonen et al. 2004; Ruckerl et al. 2005], while in toxicologic studies, particle surface area has generally been shown to be a better predictor than either particle number, mass, or volume concentration alone [Oberdörster and Yu 1990; Tran et al. 1999; Duffin et al. 2002]. A two-variable dose metric of particle size and volume has been shown to be the best predictor of lung cancer in rats from various types of particles [Borm et al. 2004; Pott and Roller 2005]. This illustrates some of the complexity of interpreting existing data on particle dose metric and response. While adverse health effects appear to be more closely related with particle surface area, the number of particles depositing in the respiratory tract or other organ systems may also play an important role.

Aerosol particle number concentration can be measured relatively easily using Condensation Particle Counters (CPCs). These are available as hand-held static instruments, and they are generally sensitive to particles greater than 10–20 nm in diameter. Condensation Particle Counters designed for the workplace do not have discrete size-selective inputs, and so they are typically sensitive to particles less than 1 μm in diameter. Commercial size-selective inlets are not available to restrict CPCs to the nanoparticle size range; however, the technology exists to construct size-selective inlets based on particle mobility or possibly on inertial pre-separation. An alternative approach to estimating nanoparticle number concentrations using a CPC is to use the instrument in parallel with an optical particle counter (OPC). The difference

is selectivity. [illegible], from sources such as combustion, vehicle emissions, and infiltration of outside air. Particle counters are generally insensitive to particle source or composition [illegible]. In a study of aerosol exposures during a carbon black bagging process, Kuhlbusch et al. [2004] found that peaks in number concentration measurements were associated with emissions from fork lift trucks and gas burners in the vicinity, rather than with the process itself. In a similar manner, during an ultrafine particle mapping exercise in an automotive facility, Peters et al. [2006] found that direct gas-fired heating systems systematically produced high particle number concentrations throughout the facility when the heating system was in operation. Through follow up measurements, Heitbrink et al. [2007] found a high proportion of ultrafine particles produced from these burners, yet little if any mass was associated with their emissions. Other non-process ultrafine sources were identified in an adjacent foundry [Evans et al. 2008]. Together with roof mounted gas-fired heating units, additional sources included cigarette-smoking and the exhaust from a propane fueled sweeper vehicle, with the latter contributing a large fraction of the ultrafine particles. Although these issues are not unique to particle number concentration measurements, orders of magnitude difference can exist in particle number concentrations depending on concomitant sources of particle emissions.

Although using nanoparticle number concentration as an exposure measurement may not be consistent with exposure metrics being used in animal toxicity studies, [illegible]. Portable CPCs are capable of measuring localized particle concentrations allowing the assessment of particle releases occurring at various processes and job tasks [Brouwer et al. 2004].

7.1.5 Surface-area estimation

Information about the relationship between different measurement metrics can be used for approximating particle surface area. If the size distribution of an aerosol remains consistent, the relationship between particle number, surface area, and mass metrics will be constant. In particular, mass concentration measurements can be used for deriving surface-area concentrations, assuming the constant of proportionality is known. This constant is the specific surface area (surface to mass ratio).

Size distribution measurements may be obtained through the collection of filter samples and analysis by transmission electron microscopy to estimate particle surface area. If the measurements are weighted by particle number, information about particle geometry will be needed to estimate the surface area of particles with a given diameter. If the measurements are weighted by mass, additional information about particle density will be required. Estimates of particle-specific surface area from geometric relation with external particle dimensions depends upon the morphology regime of the material of interest and is only appropriate for smooth, regularly shaped, compact particles [Stefaniak et al. 2003; Weibel et al. 2005]. For example, Weibel et al. [2005] report that estimates of ultrafine TiO_2

(using TEM) were 50% lower than measured using nitrogen gas adsorption.

If the airborne aerosol has a lognormal size distribution, particle surface-area concentration can be derived using three independent measurements. An approach has been proposed using three simultaneous measurements of the aerosol that included mass concentration, number concentration, and charge [Woo et al. 2001]. With knowledge of the response function of each instrument, minimization techniques can be used to estimate the parameters of the lognormal distribution leading to the three measurements used in estimating the particle surface area.

An alternative approach has been proposed whereby independent measurements of particle number and mass concentration are made, and the surface area is estimated by assuming the geometric standard deviation of the (assumed) lognormal distribution [Maynard 2003]. This method has the advantage of simplicity by relying on portable instruments that can be used in the workplace. Theoretical calculations have shown that estimates may be up to a factor of 10 different from the actual particle surface area, particularly when the aerosol has a bimodal distribution. Field measurements indicate that estimates are within a factor of 3 of the active surface area, particularly at higher concentrations. In workplace environments, particle surface-area concentrations can be expected to span up to 5 orders of magnitude; thus, surface-area estimates may be suited for initial or preliminary appraisals of occupational exposure concentrations.

Although such estimation methods are unlikely to become a long-term alternative to more accurate methods, they may provide a viable interim approach to estimating the surface area of nanoscale particles in the absence of precise measurement data. Additional research is needed on comparing methods used for estimating particle surface area with a more accurate particle surface-area-measurement method. NIOSH is conducting research in this area and will communicate results as they become available.

7.1.6 Particle number concentration mapping

TDC 0011 Td5d(il)-5(l)-6t method..n6o6article nt3(ing)li0 Td[(T3)3

facilities where sporadic or batch processing occurs.

7.2 Sampling Strategy

Currently, there is not one sampling method that can be used to characterize exposure to nanoscale aerosols. Therefore, any attempt to characterize workplace exposure to nanomaterials must involve a multifaceted approach incorporating many of the sampling techniques mentioned above. Brouwer et al. [2004] recommend that all relevant characteristics of nanomaterial exposure be measured, and a sampling strategy similar to theirs would provide a reasonable approach to characterizing workplace exposure. NIOSH has developed the Nanoparticle Emission Assessment Technique (NEAT) to qualitatively determine the release of engineered nanomaterials in the workplace (see Appendix). This approach may be helpful to others for the initial evaluation of workplaces where engineered nanomaterials are manufactured or used. If material release is found and if resources allow, then a more comprehensive and quantitative approach may be adopted [Methner et al. 2007].

The first step to characterizing workplace exposures would involve identifying the source of nanomaterial emissions. A CPC used in parallel with an OPC provides acceptable capability for this purpose. I

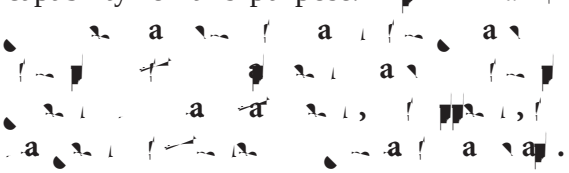

However, investigators need to be aware that

can be made to identify the nanomaterial (see Figure 7–2).

Analysis of filters for mass determination of air contaminants of interest can help identify the source of the particles. Standard analytical chemical methodologies (e.g., NMAM 5040 for carbon, NMAM 7303 for metals) should be employed [NIOSH 1994].

The combination of particle counters and samples for chemical analysis allows for an assessment of worker exposure to nanomaterials (see Figure 7–3) and the characterization of the important aerosol metrics. However, since this approach relies primarily on static or area sampling, some uncertainty will exist in estimating worker exposures.

F 7 3. Combined use of the OPC, CPC, and two filter samples to determine the presence of nanomaterials

or where a high degree of agitation is involved

- generating nanomaterials in the gas phase in non-enclosed systems
- handling (e.g., weighing, blending, spraying) powders of nanostructured materials
- maintenance on equipment and processes used to produce or fabricate nanomaterials
- cleaning up spills or waste material
- cleaning dust collection systems used to capture nanoparticles
- machining, sanding, drilling of nanomaterials, or other mechanical disruptions of nanomaterials can potentially lead to the aerosolization of nanoparticles.

8.3 Elements of a Risk Management Program

Given the limited information about the health risks associated with occupational exposure to engineered nanomaterials, appropriate steps should be taken to minimize the risk of worker exposure through the implementation of a risk management program [Schulte et al. 2008]. Risk management programs for nanomaterials should be seen

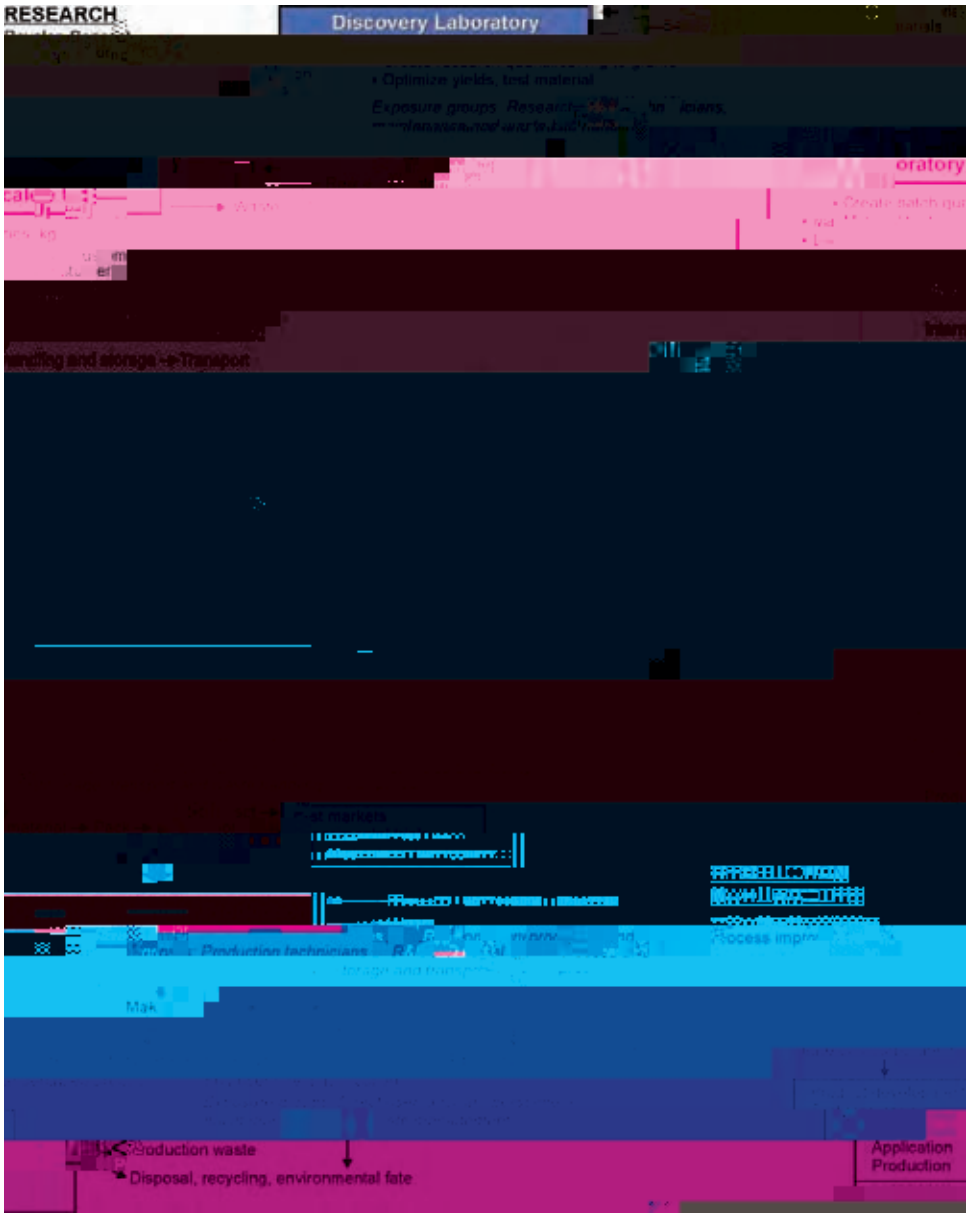

Figure 8.1. Life cycle of nanomaterials. The figure illustrates the life cycle of nanomaterials from laboratory research development through product development, use, and disposal. Each step of the life cycle represents opportunities for potential worker exposure to nanomaterials. Adapted from Schulte et al. 2008a.

account information on the potential hazardous properties of the precursor materials and intermediates as well as those of the resulting nanomaterial. In light of current scientific knowledge about the generation, transport, and capture of aerosols [Seinfeld and Pandis 1998; Hinds 1999], airborne exposure to nanomaterials can most likely be controlled at most processes and job tasks using a wide variety of engineering control techniques similar to those used in reducing exposures to general aerosols [Ratherman 1996; Burton 1997].

Engineering control techniques such as source enclosure (i.e., isolating the generation source from the worker) and local exhaust ventilation systems should be effective for capturing airborne nanomaterials, based

E6ur42o5 rohd r,2262)(hals,)30( )39(base)-2(d)]TJ s818 5(1ks73)Figolat(no8 5(1kin⁄2s)s31 >>BDC 0 -2.054 TD[(

but also varied with the size of the company, the type of nanomaterials being handled, and

data on the specific nanoparticle, and the likelihood of worker exposure (e.g., airborne concentration, time exposed, job task).

The decision to institute respiratory protection should be based on a combination of professional judgment and the results of the hazard assessment and risk management practices recommended in this document. The effectiveness of administrative, work-practice, and engineering controls can be evaluated using the measurement techniques described in Chapter 7 Exposure Assessments and Characterization. If worker exposure to airborne nanomaterials remains a concern after instituting control measures, the use of respirators can provide further worker protection. Several classes of respirators exist that can provide different levels of protection when properly fit tested on the worker. Table 8–2 lists various types of particulate respirators that can be used;3(e)-2(c)-5(t)-3(i)10(v)16(e)3(ness)-21DC T(nano)5(par) 3herly fimaeı

been conducted on larger particles and on gases/vapors with one total inward leakage (TIL) study that used nanoparticles. For example, work done by researchers at the U.S. Army RDECOM on a head-form showed that mask leakage (i.e., simulated respirator fit factor) measured using submicron aerosol challenges (0.72 μm polystyrene latex spheres) was representative of vapor challenges such as sulfur hexafluoride (SF_6) and isoamyl acetate (IAA) [Gardner et al. 2004]. Other studies using particles larger than 100 nm have shown that face seal leakage can be affected by particle size, however, the impact of this is still the subject of some debate. A recently completed laboratory study to measure TIL protection factors of four NIOSH certified N95 filtering facepiece respirator moan ⁄MCIts monend my mh(f)--3(io)3 -3(io)3(e)-82 5Be70an ⁄693(e)-82 5Be7
fa/Span 203ere.BDan ⁄MCIts mo75 /Span 017.073 0D/MCt (ßuth)-1124(42)-1124(CFR)-1124(P)35(( )

to be the worst case because these particles were considered to be in the range of the most penetrating particle size [Stevens and Moyer 1989; TSI 2005; NIOSH 1996]. However, in practice, the most penetrating particle size range (MPPS) for a given respirator can vary based on the type of filter media employed and the condition of the respirator. For example, the most penetrating particle size for N95 air purifying respirators containing electrostatically charged filter media can range from 50–100 nm [Martin and Moyer 2000; Richardson et al. 2005] to 30–70 nm [Balazy et al. 2006; Eninger et al. 2008b]. These test results were recently confirmed by NIOSH [Rengasamy et al. 2007] in which five different models of respirators with N95 filters were challenged with 11 different monodisperse NaCl particles ranging in size from 20–400 nm. The monodisperse aerosol penetrations showed that the MPPS was in the 40-nm range for all respirator models tested. Under the aggressive laboratory test conditions employed in the study, mean penetration levels for 40-nm particles ranged from 1.4%–5.2%, which suggested that the respirators would be effective at capturing nanoparticles in the workplace. The NIOSH study also investigated whether there was a correlation between filtration performance using the existing NIOSH certification protocol for N series air purifying respirators and the filtration performance against monodisperse particles at the MPPS. A good correlation ($r = 0.95$) was found (e.g., respirators that performed better using the NIOSH certification test also had higher filter efficiencies against monodisperse 40-nm nanoparticles), which is not surprising given that changes in filtration performance follow a consistent trend as a function of particle size.

-

selection process, perhaps by choosing a respirator with higher levels of filtration performance (e.g., changing from an N95 to a P100, even though the APF will remain the same) as suggested by OSHA [Federal Register 2006] or by selecting a respirator with a higher APF (e.g., full face-piece respirator or powered air purifying respirator). Dust masks, commercially available at hardware/home improvement stores, are often con-

Table 8-2 (Continued). Advantages and disadvantages of respirators

Respirator type	NIOSH assigned protection factor	Advantages	Disadvantages
Elastomeric full-facepiece with N-100, R-100, or P-100 filters	50	– Provides eye protection – Low maintenance – Reusable facepiece and replaceable filters and cartridges – No effect on mobility – More effective face seal than that of filtering facepiece or elastomeric half-facepiece respirators	– Can add to heat burden – Diminished field-of-vision compared to half-facepiece –Inward leakage at gaps in face seal –Fit testing required to select proper facepiece size –Facepiece lens can fog without nose cup or lens treatment –Spectacle kit needed for people who wear corrective glasses
Powered with tight-fitting half-facepiece or full-facepiece	50	–Provides eye protection with full-facepiece –Low breathing resistance –Face seal leakage is generally outward –Flowing air creates cooling effect –Reusable components and replaceable filters	–Added weight of battery and blower

Occupational health surveillance is an essential component of an effective occupational safety and health program. The unique physical and chemical properties of nanomaterials, the increasing growth of nanotechnology in the workplace, and information suggesting that exposure to some engineered nanomaterials can cause adverse health effects in laboratory animals all support consideration of an occupational health surveillance program for workers potentially exposed to engineered nanomaterials [Schulte et al. 2008a]. Continued evaluation of toxicologic research and workers potentially exposed to engineered nanomaterials is needed to inform NIOSH and other groups regarding the appropriate components of occupational health surveillance for nanotechnology workers.

NIOSH has developed interim guidance relevant to medical screening (one component of an occupational health surveillance program) for nanotechnology workers (see NIOSH Current Intelligence Bulletin: *Interim Guidance on Medical Screening and* *eazar16(e)-4245Silrq2@lo8EMC alo8EMC and lo868Span K1 1 T 72g162(e)*

utility of establishing exposure registries for workers potentially exposed to engineered nanomaterials.

— Assess the feasibility of industry-wide exposure and epidemiological studies of workers exposed to engineered nanomaterials, with emphasis on workers potentially exposed to engineered carbonaceous nanomaterials.

— Integrate nanotechnology safety and health issues into existing hazard surveillance mechanisms and continue reassessing guidance related to occupational health surveillance for workers potentially exposed to engineered nanomaterials.

— Build on existing public health geographical information systems and infrastructure to enable effective and economic development of methods for sharing nanotechnology safety and health data.

4. R A

— Determine how existing exposure-response data for fine and ultrafine particles (human or animal) may be used to identify the potential hazards and estimate the potential risks of occupational exposure to nanomaterials.

— Develop a framework for assessing the potential hazards and risks of occupational exposure to nanomaterials, using new toxicologic data on engineered nanomaterials and standard risk assessment models and methods.

5. M M

— Evaluate methods used to measure the mass of respirable particles in the air and determine whether this measurement can be used to measure nanomaterials.

— Develop and field-test practical methods to accurately measure airborne nanomaterials in the workplace.

— Develop, test, and evaluate systems to compare and validate sampling.

6. E C a P a P E

— Evaluate the effectiveness of engineering controls in reducing occupational exposures to nanoaerosols and developing new controls when needed.

— Evaluate the suitability of control-banding techniques when additional information is needed and evaluate the effectiveness of alternative materials.

— Evaluate and improve current personal protective equipment.

— Develop recommendations (e.g., use of respiratory protection) to prevent or limit occupational exposures to nanomaterials.

7. F a E Sa

— Identify physical and chemical properties that contribute to dustiness, combustibility, flammability, and conductivity of nanomaterials.

— Recommend alternative work practices to eliminate or reduce work place exposures to nanomaterials.

8. R [illegible] a [illegible] G [illegible] a

— Use the best available science to make interim recommendations for workplace safety and health practices during the production, use, and handling of nanomaterials.

Evaluate and update mass-iocdjEM/Span ⁄AMCIak prac

ACGIH [2001]. Industrial ventilation: a manual of recommended practice. Cincinnati, OH: American Conference of Governmental Industrial Hygienists.

Adams RJ, Bray D [1983]. Rapid transport of foreign particles microinjected into crab axons. Nature *303*:718–720.

Ambroise D, Wild P, Moulin J-J [2007]. Update of a meta-analysis on lung cancer and welding. Scand J Work Environ Health *32*(1):22–31.

Antonini JM [2003]. Health effects of welding. Crit Rev Toxicol *33*(1):61–103.

ASTM Subcommittee F23.40 [2003]. Standard test method for resistance of materials used in protective clothing to penetration by blood-borne pathogens using Phi–X174 bacteriophage penetration as a test system. West Conshohocken, PA: American Society for Testing and Materials, ASTM F1671–03.

ASTM Committee E2535–07 [2007]. Standard guide for handling unbound engineered nanoscale particles in occupational settings. West Conshohocken, PA: ASTM International.

Balazy A, Toivola M, Reponen T, Podgorski A, Zimmer A, Grinshpun SA [2006]. Manikin-based filtra-

ASTM Comm4/MCID 54419.364DC -2[(sk]TJh2[(P)81(A:)10( )20(ASTM I)15(A,)30( )-19.364Dalazy)(alazy2(alai-8(at)nzy)(asistanc>603.

Castranova V [2000]. From coal mine dust to quartz: mechanisms of pulmonary pathogenicity. Inhal Tox *12*(Suppl 3):7–14.

Daigle CC, Chalupa DC, Gibb FRMorrow PE, Oberdorster G, Utell MJ, Frampton MW [2003]. Ultrafine particle deposition in humans during rest and exercise. Inhal Toxicol *15*(6):539–552.

De Lorenzo AJD [1970]. The olfactory neuron and the blood-brain barrier. In: Wolstenholme GEW, Knight J, eds. Taste and smell in vertebrates. CIBA Foundation Symposium series. London: J&A Churchill, pp. 151–176.

Dockery DW, Pope CA, Xu X, Spengler JD, Ware JH, Fay ME, Ferris BG, Speizer BE [1993]. An association between air pollution and mortality in six U.S. cities. N Engl J Med *329*(24):1753–1759.

Donaldson K, Li XY, MacNee W [1998]. Ultrafine (nanometer) particle mediated lung injury. J Aerosol Sci *29*(5–6):553–560.

Donaldson K, Tran CL [2002]. Inflammation caused by particles and fibers. Inhal Toxicol *14*(1):5–27.

Donaldson K, Stone V [2003]. Current hypotheses on the mechanisms of toxicity of ultrafine particles. Ann 1st Super Sanita *39*(3):405–410.

Donaldson K, Tran L, Jimenez LA, Duffin R, Newby DE, Mills N, MacNee W, Stone V [2005]. Combustion-derived nanoparticles: a review of their toxicology following inhalation exposure. Part Fibre Toxicol. *2*(10):14.

Donaldson K, Aitken R, Tran L, Stone V, Duffin R, Forrest G, Alexander A [2006]. Carbon nanotubes: a review of their properties in relation to pulmonary toxicology and workplace safety. Toxicol Sci *92*(1):5–22.

Driscoll KE [1996]. Role of inflammation in the development of rat lung tumors in response to chronic particle exposure. In: Mauderly JL, McCunney RJ, eds. Particle overload in the rat lung and lung cancer: implications for human risk assessment. Philadelphia, PA: Taylor & Francis, pp. 139–152.

Duffin R, Tran CL, Clouter A, Brown DM, MacNee W, Stone V, Donaldson K [2002]. The importance of surface area and specific reactivity in the acute pulmonary inflammatory response to particles. Ann Occup Hyg *46*:242–245.

Duffin R, Tran L, Brown D, Stone V, Donaldson K [2007]. Proinflammogenic effects of low-toxicity and metal nanoparticles in vivo and in vitro: highlighting the role of particle surface area and surface reactivity. Inhal Toxicol *19*(10):849–856.

Edlich RF, Suber F, Neal JG, Jackson EM, Williams FM [1999]. Integrity of powder-free gloves to bacteriophage penetration. J Biomed Mater Res B Appl Biomater *48*:755–758.

Elder A, Gelein R, Silva V, Feikert T, Opanashuk L, Carter J, Potter R, Maynard A, Ito Y, Finkelstein J, Oberdörster G [2006]. Translocation of inhaled ultrafine manganese oxide particles to the central nervous system. Environ Health Perspect *114*:1172–1178.

Eninger RM, Honda T, Reponen T, McKay R, Grinshpun SA [2008a]. What does respirator certification tell us about filtration of ultrafine particles? J Occup Environ Hyg *5*:286–295.

Eninger RM, Honda T, Adhikari A, Heinonen-Tanski H, Reponen T, Grinshpun SA [2008b]. Filter performance of N99 and N95 facepiece respirators against viruses and ultrafine particles. Ann Occup Hyg *52*(5):385–396.

71 Fed. Reg. 50121–50192 [2006]. Occupational Safety and Health Administration: assigned protection factors, final rule [www.osha.gov/pls/oshaweb/owadisp.show_document?p_table=FEDERAL_REGISTER&p_id=18846].

European Committee for Standardization [2002]. CEN 943–1:2002: Protective clothing against liquid and gaseous chemicals, aerosols and solid particles. Performance requirements for ventilated and non-ventilated "gas-tight" (Type 1) and "non-gas-tight" (Type 2) chemical protective suits. Brussels: European Committee for Standardization.

Evans DE, Heitbrink WA, Slavin TJ, Peters TM [2008]. Ultrafine and respirable particles in an automotive grey iron foundry. Ann Occup Hyg *52*(1):9–21.

Frampton MW, Stewart JC, Oberdorster G, Morrow PE, Chalupa D, Pietropaoli AP, Frasier LM, Speers DM, Cox C, Huang LS, Utell MJ [2006]. Inhalation of ultrafine particles alters blood leukocyte expression of adhesion molecules in humans. Environ Health Perspect *114*(1):51–58.

Fuchs NA [1964]. The mechanics of aerosols. Oxford, England: Pergamon Press.

Gao P, King WP, Shaffer R [2007]. Review of chamber design requirements for testing of personal protective clothing ensembles. J Occup & Environ Hyg *4*(8):562–571.

Gardiner K, van Tongeren M, Harrington M [2001]. Respiratory health effects from exposure to carbon black: results of the phase 2 and 3 cross sectional studies in the European carbon black manufacturing industry. Occup Environ Med *58*(8):496–503.

Gardner P, Hofacre K, Richardson A [2004]. Comparison of simulated respirator fit factors using aerosol and vapor challenges. J Occup and Environ Hyg *1*(1):29–38.

Garshick E, Laden F, Hart JE, Rosner B, Smith TJ, Dockery DW, Speizer FE [2004]. Lung cancer in railroad workers exposed to diesel exhaust. Environ Health Perspect *112*(15):1539–1543.

Garshick E, Laden F, Hart JE, Smith TJ, Rosner B [2006]. Smoking imputation and lung cancer in railroad workers exposed to diesel exhaust. Am J Ind Med *49*(9):709–718.

Geiser M, Rothen-Rutishauser B, Kapp N, Schurch S, Kreyling W, Schulz H, Semmler M, Im Hof V, Heyder J, Gehr P [2005]. Ultrafine particles cross cellular membranes by nonphagocytic mechanisms in lungs and in cultured cells. Environ Health Perspect *113*(11):1555–1560.

Golanski L, Guiot A, Tardif F [2008]. cup T*[(l)5(ung)-6(s)-45(an36/Span <</MCID 5713 >>BDC /T1_1 1 Tf(49)TjEMC /S37n <</MCID 5714 >>B
lul47 membranes in V7(wa(o)3(n)-45(En)2 E)-12(bse)-23(n(sp) ran o)1hubse

Ibald-Mulli A, Wichmann HE, Kreyling W, Peters A [2002]. Epidemiological evidence on health effects of ultrafine particles. J Aerosol Med Depos *15*(2):189–201.

International Council on Nanotechnology (ICON) [2006]. A survey of current practices in the nanotechnology workplace. [http://cohesion.rice.edu/CentersAndInst/ICON/emplibrary/ICONNanotechSurveyFullReduced.pdf].

ICRP [1994]. Human respiratory tract model for radiological protection. Oxford, England: Pergamon, Elsevier Science Ltd., International Commission on Radiological Protection, Publication No. 66.

ISO [2004a]. Protective clothing for use against solid particulates. Part 2: Test method of determination of inward leakage of aerosols of fine particles into suits. ISO Standard 13982–2. Geneva, Switzerland: International Organization for Standardization.

ISO [2004b]. ISO 16604:2004: Clothing for protection

Lee KP, Trochimowicz HJ, Reinhardt CF [1985]. Pulmonary response of rats exposed to titanium dioxide (TiO_2) by inhalation for two years. Toxicol Appl Pharmacol *79*:179–192.

Lee CH, Guo YL, Tsai PJ, Chang HY, Chen CR, Chen CW, Hsiue TR [1997]. Fatal acute pulmonary oedema after inhalation of fumes from polytetrafluoroethylene (PTFE). Eur Res J *10*:1408–1411.

Lee SA, Grinshpun SA, Reponen T [2008]. Respiratory performance offered by N95 respirators and surgical masks: Human subject evaluation with NaCl aerosol representing bacterial and viral particle size range. Ann Occup Hyg *52*(3):177–85. Epub 2008 Mar 7.

Lippmann M [1977]. Regional deposition of particles in the human respiratory tract. In: Lee DHK, Murphy S, eds. Handbook of physiology; section IV, environmental physiology. Philadelphia, PA: Williams and Wilkins, pp. 213–232.

Li N, Sioutas C, ChMC hM/M3(W)35(ilmgMC 0 TdTD[(Li)-70J4)-70J4l

Moller W, Brown DM, Kreyling WG, Stone V [2005]. Ultrafine particles cause cytoskeletal dysfunctions in macrophages: role of intracellular calcium. Part Fibre Toxicol *2*(7):12.

Monteiro-Riviere NA, Nemanich RJ, Inman AO, Wang YY, Riviere JE [2005]. Multi-walled carbon nanotube interactions with human epidermal keratinocytes. Toxicol Lett *155*(3):377–384.

Moshammer H, Neuberger M [2003]. The active surface of suspended particles as a predictor of lung function and pulmonary symptoms in Austrian school children. Atmos Environ *37*(13):1737–1744.

Mossman B, Churg A [1998]. Mechanisms in the pathogenesis of asbestosis and silicosis. Am J Respir Crit Care Med *157*:1666–1680.

Muller J, Huaux F, Moreau N, Misson P, Heilier J-F, Delos M, Arras M, Fonseca A, Nagy JB, Lison D [2005]. Respiratory toxicity of multi-wall carbon nanotubes. Toxicol Appl Pharmacol *207*:221–231.

Murray AR, Kisin E, Kommineni C, Kagan VE, Castranova V, Shvedova AA [2007]. Single-walled carbon nanotubes induce oxidative stress and inflammation in skin. Toxicologist *96*:A1406.

National Fire Protection Association (NFPA) [2007]. NFPA 1994 standard on protective ensembles for first responders to CBRN terrorism incidents.

Nel A, Xia T, Madlen L, Li W [2006]. Toxic potential of materials at the nanolevel. Science *311*:622–627.

Nemmar A, Hoet PHM, Vanquickenborne B, Dinsdale D, Thomeer M, Hoylaerts MF, Vanbilloen H, Mortelmans L, Nemery B [2002]. Passage of inhaled particles into the blood circulation in humans. Circulation *105*:411–414.

NIOSH [1990]. NIOSH testimony on the Occupational Safety and Health Administration proposed rule on health standards: methods of compliance. Cincinnati, OH: U.S. Department of Health and Human Services, Centers for Disease Control, National Institute for Occupational Safety and Health.

NIOSH [1994]. NIOSH manual of analytical methods (NMAM®). 4th ed. By Schlecht PC, O'Connor PF, eds. Cincinnati, OH: U.S. Department of Health and Human Services, Centers for Disease Control and Prevention, National Institute for Occupational Safety and Health, DHHS (NIOSH) Publication 94–113 [www.cdc.gov/niosh/nmam/].

NIOSH [1996]. NIOSH guide to the selection and use of particulate respirators certified under 42 CFR 84. Cincinnati, OH: U.S. Department of Health and Human Services, Centers for Disease Control and Prevention, National Institute for Occupational Safety and Health, DHHS (NIOSH) Publication No. 96–101.

NIOSH [2003]. Filtration and air-cleaning systems to protect building environments. Cincinnati, OH: U.S. Department of Health and Human Services, Centers for Disease Control and Prevention, National Institute for Occupational Safety and Health, DHHS (NIOSH) Publication No. 2003–136.

NIOSH [2004]. NIOSH respirator selection logic. Cincinnati, OH: U.S. Department of Health and Human Services, Centers for Disease Control and Prevention, National Institute for Occupational Safety and Health, DHHS (NIOSH) Publication No. 2005–100 [www.cdc.gov/niosh/docs/2005-100/].

NIOSH [2005a]. Procedure No. RCT–APR–STP–0057, 0058, 0059, Revision 1.1. Cincinnati, OH: Department of Health and Human Services, Centers for Disease Control and Prevention, National Institute for Occupational Safety and Health [www.cdc.gov/niosh/npptl/stps/pdfs/RCT-APR-0057%2058%2059.pdf].

NIOSH [2005b]. Procedure No. RCT–APR–STP–0051, 0052, 0053, 0054, 0055, 0056, Revision 1.1. Cincinnati, OH: Department of Health and Human Services, Centers for Disease Control and Prevention, National Institute for Occupational Safety and Health [www.cdc.gov/niosh/npptl/stps/pdfs/RCT-APR-0051%2052%2053%2054%2055%2056.pdf].

NIOSH [2009]. Current intelligence bulletin: interim guidance on medical screening of workers potentially exposed to engineered nanoparticles. Cincinnati, OH: U.S. Department of Health and Human Services, Centers for Disease Control and Prevention, National Institute for Occupational Safety and Health [www.cdc.gov/niosh/docs/2009-116/].

NIOSH [2007]. Docket Number 036: Total Inward Leakage Test for Half-Mask Air-Purifying Particulate Respirators; Total Inward Leakage Test for Half-mask Air-purifying Particulate Respirators. Procedure No.

clearance kinetics of inhaled ultrafine insoluble iridium particles from the rat lung, including transient translocation into secondary organs. Inhal Toxicol *16*(6–7):453–459.

Shalev I, Barker RL, McCord MG, Tucker PA, Lisk BR [2000]. Protective textile particulate penetration screening. Performance of protective clothing: 7th Symposium, ASTM STP 1386, West Conshohocken, PA: American Society for Testing and Materials, ASTM pp. 155–161.

Shiohara A, Hoshino A, Hanaki K, Suzuki K, Yamamoto K [2004]. On the cytotoxicity of quantum dots. Microbiol Immunol *48*(9):669–675.

Shvedova AA, Kisin ER, AR Murray, Gandelsman VZ, Maynard AD, Baron PA, Castranova V [2003]. Exposure to carbon nanotube material: assessment of the biological effects of nanotube materials using human keratinocyte cells. J Toxicol Environ Health *66*(20):1909–1926.

Shvedova AA, Kisin ER, Murray AR, Schwegler-Berry D, Gandelsman VZ, Baron P, Maynard A, Gunther MR, Castranova V [2004]. Exposure of human bronchial epithelial cells to carbon nanotubes cause oxidative stress and cytotoxicity. In: Proceedings of

of lung Clara cell protein CC16. Occup Environ Med *61*(11):908–914.

Tinkle SS, Antonini JM, Rich BA, Robert JR, Salmen R, DePree K, Adkins EJ [2003]. Skin as a route of exposure and sensitization in chronic beryllium disease. Environ Health Perspect *111*(9):1202–1208.

Törnqvist H, Mills NL, Gonzalez M, Miller MR, Robinson SD, Megson IL, Macnee W, Donaldson K, Söderberg S, Newby DE, Sandström T, Blomberg A [2007]. Persistent endothelial dysfunction in humans after diesel exhaust inhalation. Am J Respir Crit Care Med *176*(4):395–400.

Tran CL, Cullen RT, Buchanan D, Jones AD, Miller BG, Searl A, Davis JMG, Donaldson K [1999]. Investigation and prediction of pulmonary responses to dust, part II. In: Investigations into the pulmonary effects of

Borm PJA [2002]. Particle toxicology: from coal mining to nanotechnology. Inhal Toxicology *14*:311–324.

Byrd DM, Cothern CR [2000]. Introduction to risk analysis. Rockville, MD: Government Institutes.

Castranova V [1998]. Particles and airways: basic biological mechanisms of pulmonary pathogenicity. Appl Occup Environ Hyg *13*(8):613–616.

Conhaim RL, Eaton A, Staub NC, Heath TD [1988]. Equivalent pore estimate for the alveolar-airway barrier in isolated dog lung. J Appl Physiol *64*(3):1134–1142.

Driscoll KE, Costa DL, Hatch G, Henderson R, Oberdörster G, Salem H, Schlesinger RB [2000]. Intratracheal instillation as an exposure technique for the evaluation of respiratory tract toxicity: uses and limitations. Toxicol Sci *55*(1):24–35.

EC [2004]. Nanotechnologies: a preliminary risk analysis on the basis of a workshop organized in Brussels, March 1–2, 2004, by the Health and Consumer Protection Directorate General of the European Commission. Brussels, Germany: European Commission [http://www.certh.gr/dat/7CF3F1C6/file.pdf?633556363252496250].

EPA [1992]. Guidelines for exposure assessment. Washington, DC: U.S. Environmental Protection Agency.

Faux SP, Tran CL, Miller BG, Jones AD, Monteiller C, Donaldson K [2003]. In vitro determinants of particulate toxicity: the dose-metric for poorly soluble dusts. Research report 154. Suffolk, UK: Health and Safety Executive.

Ferin J, Oberdörster G [1992]. Translocation of particles from pulmonary alveoli into the interstitium. J Aerosol Med *5*(3):179–187.

Gibbs JP, Crump KS, Houck DP, Warren PA, Mosley WS [1999]. Focused medical surveillance: a search for subclinical movement disorders in a cohort of U.S. workers exposed to low levels of manganese dust. Neurotoxicol *20*(2–3):299–313.

Hardman R [2006]. A toxicologic review of quantum dots: toxicity depends on physicochemical and environmental factors. Environ Health Perspect *114*(2):165–172.

Hayes AW, ed. [2001]. Principles and methods of toxicology. 4th ed. Philadelphia, PA: Taylor and Francis.

Hoet PHM, Bruske-Hohlfeld I, Salata OV [2004]. Nanoparticles-known and unknown health risks. J Nanobiotech *2*(12):1–15.

Hofmann W, Sturm R, Winkler-Heil R, Pawlak E [2003]. Stochastic model of ultrafine particle deposition and clearance in the human respiratory tract. Radiat Prot Dosim *105*(1–4):77–80.

Hood E [2004]. Nanotechnology: looking as we leap. Environ Health Perspect *112*(13):A741–A749.

Huckzko A, Lange H [2001]. Carbon nanotubes: experimental evidence for a null risk of skin irritation and allergy. Fullerene Sci Tech *9*(2):247–250.

Huckzko A, Lange H, Calko E, Grubeck-Jaworska H, Droszez P [2001]. Physiological testing of carbon nanotubes: are they asbestos-like? Fullerene Sci Tech *9*(2):251–254.

Keller A, Fierz M, Siegmann K, Siegmann HC, Filippov A [2001]. Surface science with nanosized particles in a carrier gas. J Vac Sci Technol A *19*(1):1–8.

Klaassen CD, Amdur MO, Doull J [1986]. Casarett and Doull's toxicology: the basic science of poisons. New York: Macmillan Publishing Company.

Last JM [1983]. A dictionary of epidemiology. New York: Oxford University Press.

Lee KW, Liu BYH [1981]. Experimental study of aerosol filtration by fibrous filters. Aerosol Sci Technol *1*(1):35–46.

Lee KW, Liu BYH [1982]. Theoretical study of aerosol filtration by fibrous filters. Aerosol Sci Technol *1*(2):147–162.

Li N, Sioutas C, Cho A, Schmitz D, Misra C, Sempf J, Wang MY, Oberley T, Froines J, Nel A [2003]. Ultrafine particulate pollutants induce oxidative stress and mitochondrial damage. Environ Health Perspect *111*(4):455–460.

Maynard AD [2001]. Experimental determination of ultrafine TiO_2 de-agglomeration in surrogate pulmonary surfactant—preliminary results. Inhaled Particles IX, Cambridge, UK: The British Occupational Hygiene Society.

Maynard AD [2002]. Experimental determination of ultrafine TiO_2 de-agglomeration in surrogate pulmonary surfacr 10(a)10(n)10.6accal

1.0 Introduction

This appendix describes a technique that can be used by industrial hygienists for conducting initial workplace assessments for possible nanoparticle emissions. It allows a semi-quantitative evaluation of processes and tasks in the workplace where releases of engineered nanoparticles may occur. NIOSH uses several sampling approaches simultaneously with the goal of obtaining key physicochemical particle metrics: number concentration, qualitative size, shape, degree of agglomeration, and mass concentration of elemental constituents of interest.

2.0 Scope

Employers, workers, and researchers engaged in the production and use of engineered nanomaterials have expressed an interest in determining whether these nanomaterials are hazardous and if the potential for worker exposure exists. NIOSH has an

airborne releases of engineered nanomaterials occur. This assessment, which compares particle number concentrations and relative particle size at the potential emission source to background particle number concentrations and particle size, provides a semi-quantitative means for determining the effectiveness of existing control measures in reducing engineered nanoparticle exposures. This procedure utilizes portable direct-reading instrumentation supplemented by filter-based air samples (source-specific and personal breathing zone [PBZ]). The use of filter samples is crucial for particle identification because direct-reading instruments used for determining particle number concentrations are incapable of identifying the composition of the particles.

3.0 Summary of the On-Site Initial Assessment

The initial assessment uses a combination of direct-reading, handheld instruments (CPC and OPC) and filter-based sampling (e.g. 37-mm diameter filter cassettes) for subsequent chemical and microscopic analyses (Figure 1). This semi-quantitative approach was first described by Maynard et al. [2004] and NIOSH has adopted a similar approach. The technique includes determining particle number concentration using direct-reading, handheld particle counters at potential emission sources and comparing those data to background particle number concentrations. If elevated concentrations of suspect-

of air independent of chemical identity within six specific size ranges. The OPC used by the NIOSH field research team provides particle counts in the following size cut-points: 300 nm; 500 nm; 1,000 nm; 3,000 nm; 5,000 nm; and 10,000 nm. The range of detection for this instrument is reported by the manufacturer to be 0−70,000 P/L. Different manufacturers' OPCs may have slightly different particle size ranges and could be substituted.

4.3 Appropriate air sampling filter media (e.g. mixed cellulose ester, quartz fiber filter) are selected depending on nanoparticle type and desired analytical information (e.g., determination of particle morphology using TEM or SEM, elemental analysis for metals, elemental analysis for carbon)

4.4 Air sampling pumps capable of sampling at high flow rates (e.g., 7 liters per minute or other flow rate depending upon the duration of the task and the appropriate NIOSH method, if a method is available)

4.5 Sampling pump flow calibrator

4.6 If desired, personal cascade impactor
Ifd, or C /Sre

- Determines the presence/absence of general and local exhaust ventilation and other engineering controls. (This initial assess-

made with the CPC and OPC simultaneously at locations near the suspected or likely emission source (e.g., opening a reactor, handling product, potential leak points in the ventilation system). Airborne particle concentrations are determined before, during, and after each task or operation to identify those factors (e.g., controls, worker interaction, work practices) that may affect airborne particle concentrations. This information is used to identify processes, locations, and personnel for filter-based air sampling (5.3).

5.3 Conduct Filter-based Area and Personal Air Sampling

5.3.1 *Area air sampling*

A pair of filter-based, air samples are collected at process/task locations and/or workers engaged in process operations where suspected engineered nanomaterial emissions may occur, based on air sampling results using the CPC and OPC.

Filter-based area air samples provide more specific information on the engineered nanomaterial of interest (e.g., size, shape, mass). The pair of air samples includes one sample analyzed for elemental mass and one sample analyzed by electron microscopy. For example, one sample might be collected for metals determination (e.g., NIOSH Method 7300, 7303) or elemental carbon (e.g., NIOSH Method 5040) depending on the composition of the engineered nanomaterial. The other sample would be collected for particle characterization

of dispersion (e.g., degree of agglomeration) by TEM or SEM using the measurement techniques specified in NIOSH Methods 7402,

infiltration of outside air. Particle counters are generally not selective to particle source or composition, making it difficult to differentiate between incidental and process-related nanoparticles using number concentration alone. The CPC and OPC are used to identify sources of nanoparticles and the filter-based samples are used to verify the size, shape, and chemical composition of the nanoparticles with the goal of differentiating between incidental and engineered nanoparticles.

5.5.2 *Limitations*

The exposure assessment technique does have some limitations including:

- Although this issue is not unique to particle number concentration measurements, orders of magnitude difference can exist in aerosol number concentrations, depending on the number and types of sources of particle emissions. Monitoring over several days and during different seasons can provide a better understanding of the variability that might exist in airborne particle number concentrations found in background measurements and in measurements made at sources where engineered nanomaterials are handled.
- The upper dynamic range of the CPC is 100,000 P/cm^3. A dilutor, consisting of a modified HEPA filter cartridge placed upstream of the inlet, can extend the range of the CPC when particle number concentrations are greater than 100,000 P/cm^3 [Peters et al. 2006; Heitbrink et al. 2007; Evans et al. 2008].
- The analysis of air samples by TEM or SEM with energy dispersive X-ray spectrometry can provide information on the elemental composition of the nanomaterials. However, TEM and SEM analysis can be compromised if there is particle overload on the filter. Alternatively, if the loading is too sparse, an accurate assessment of par-

a facility or easily worn by a worker to provide an indication of PBZ exposure. Additionally, there is no single instrument capable of measuring the numerous potential exposure metrics associated with engineered nanomaterials (e.g., number concentration, surface area, size, shape, mass concentration) [Maynard and Aitken 2007]. Although the following instruments lack field portability and ease of use, they can measure many of the desirable exposure metrics and provide information about the particle size distribution. These research-grade particle analyzers are not usually part of the initial assessment but are used when additional knowledge about the nanoscale particle temporal or spatial exposure variation or size distribution is desired.

5.6.1.1 *Particle Surface-Area Analyzers*

Toxicology studies have indicated that surface area of nanoparticles may be an important exposure dose metric.

Gloves and template are discard

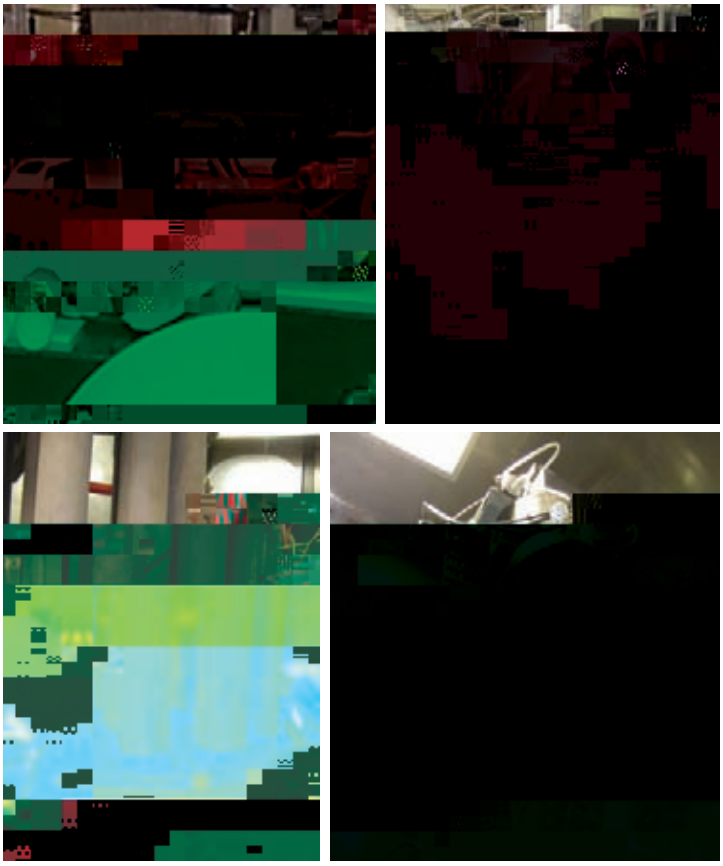

F 1. A demonstration of the initial assessment technique with side-by-side sampling using (from left to right) the OPC, co-located open-face filter cassettes, and the CPC: examples of PBZ and source-specific filter-based sampling setup.

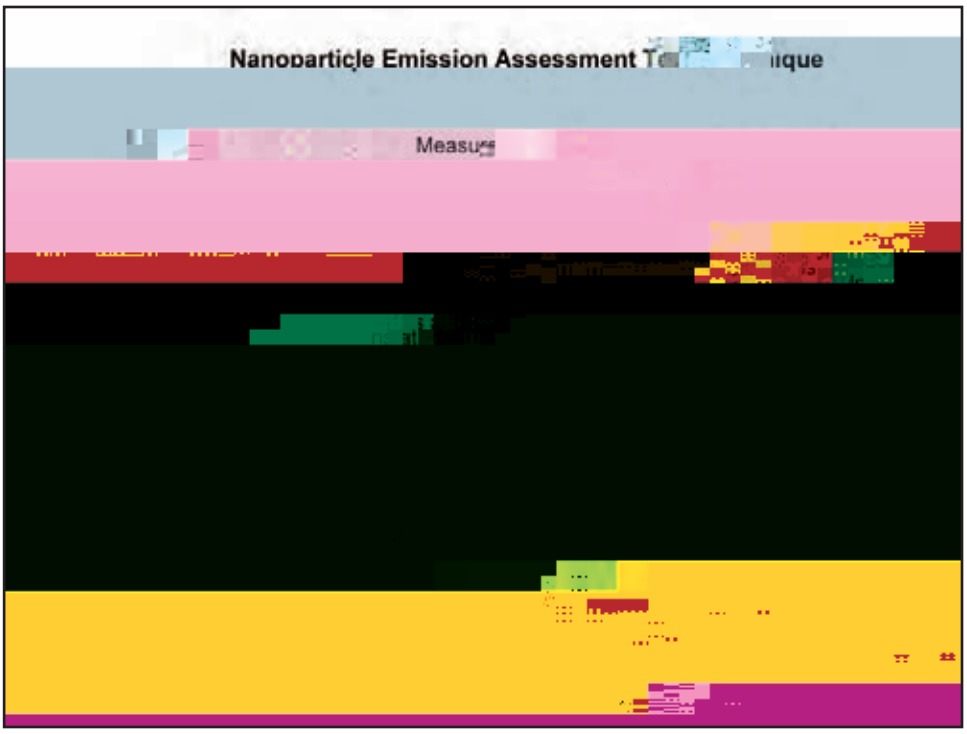

F 2. Summary of the initial assessment technique

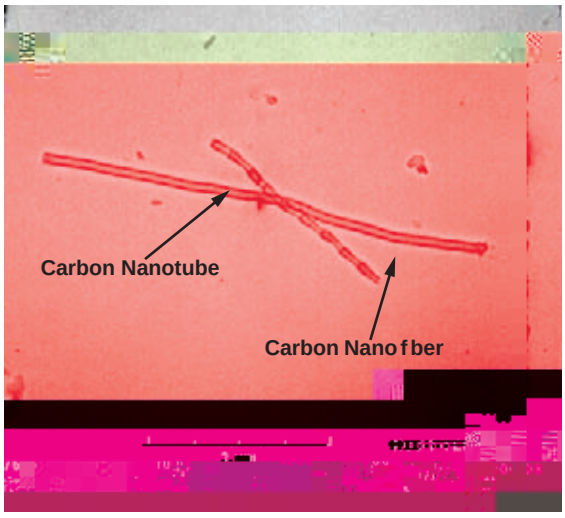

F 3. Electron microscopy micrograph of a carbon nanofiber

F 4. Electron microscopy micrograph of a carbon nanofiber and carbon nanotube

1–800–CDC–INFO (1 00 232 3)
. 1 232 3

www.cdc.gov/niosh.

eNews **www.cdc.gov/niosh/eNews**.

DHHS (NIOSH) Publication No. 2009–125